

Second edition
2015-10-01

AMENDMENT 1
2020-10

Plastics piping systems for industrial applications — Polybutene (PB), polyethylene (PE), polyethylene of raised temperature resistance (PE-RT), crosslinked polyethylene (PE-X), polypropylene (PP) — Metric series for specifications for components and the system

AMENDMENT 1

Systèmes de canalisations en matières plastiques pour les applications industrielles — Polybutène (PB), polyéthylène (PE), polyéthylène de meilleure résistance à la température (PE-RT), polyéthylène réticulé (PE-X), polypropylène (PP) — Séries métriques pour les spécifications pour les composants et le système

AMENDEMENT 1



Reference number
ISO 15494:2015/Amd.1:2020(E)

© ISO 2020

STANDARDSISO.COM : Click to view the full PDF of ISO 15494:2015/Amd 1:2020



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 3, *Plastics pipes and fittings for industrial applications*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 155, *Plastic piping systems and ducting systems*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

STANDARDSISO.COM : Click to view the full PDF of ISO 15494:2015/Amd 1:2020

Plastics piping systems for industrial applications — Polybutene (PB), polyethylene (PE), polyethylene of raised temperature resistance (PE-RT), crosslinked polyethylene (PE-X), polypropylene (PP) — Metric series for specifications for components and the system

AMENDMENT 1

D.1.1

Replace [Formula \(D.1\)](#) with the following:

$$\log t = -105,8618 - \frac{18506,15 \log \sigma}{T} + \frac{57895,49}{T} - 24,7997 \log \sigma \quad (\text{D.1})$$

Modify the NOTE as follows:

NOTE The calculation for PE-X is based on ISO 10146 but in this document the logarithm to base 10 is indicated with log, where $\log = \log_{10} = \lg$.


At the end of the subclause, add the following text:

The 110 °C values have been determined separately using water inside and air outside the test specimen. The reference line is described by [Formula \(D.2\)](#):

$$\log t = 37,4958 - 84,0336 \log \sigma \quad (\text{D.2})$$

D.1.1.1

Replace [Figure D.1](#) with the following figure:

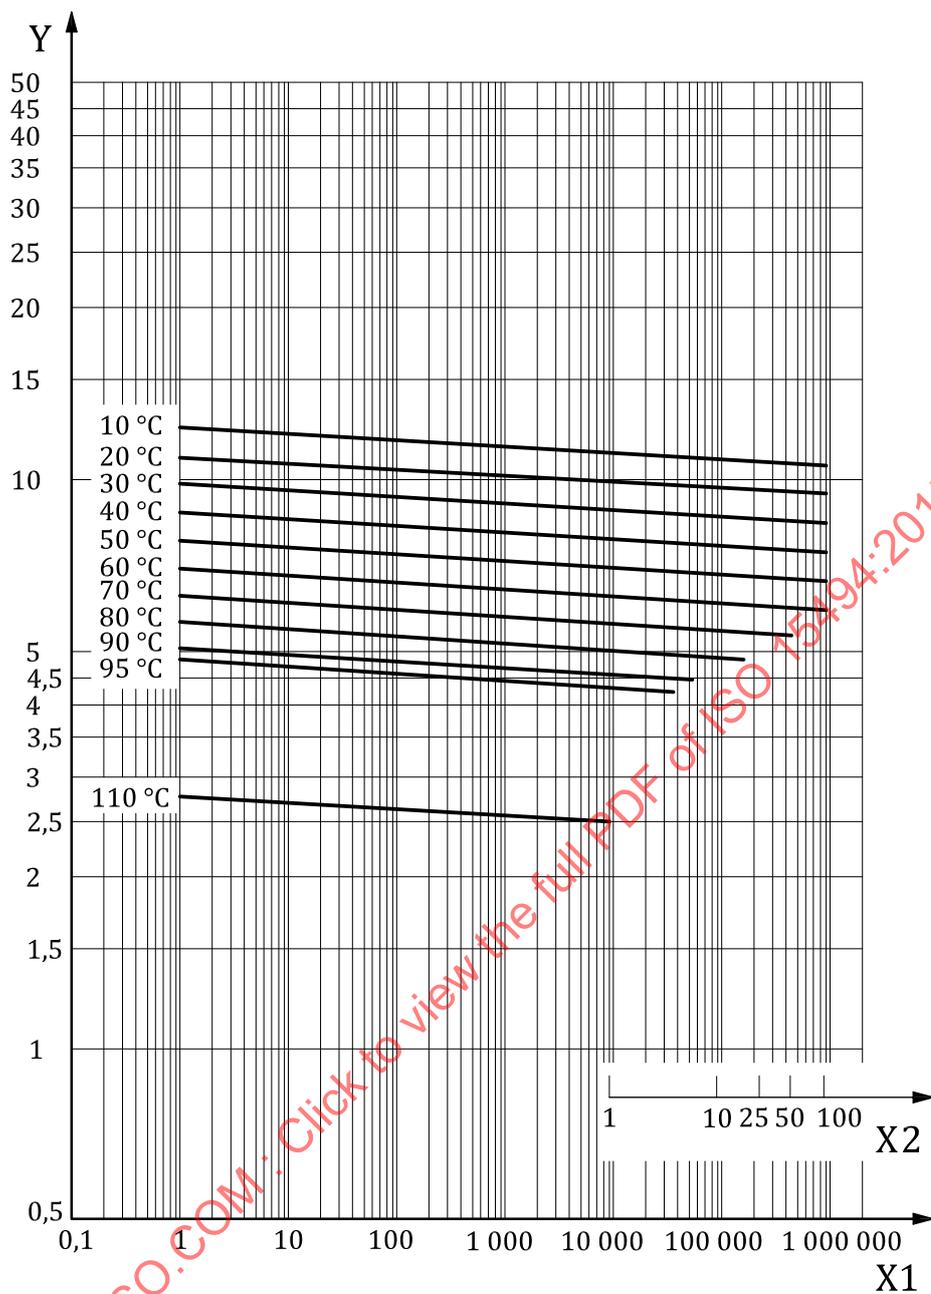

Key

- X₁ time to failure, in hours (h)
- X₂ time to failure, in years
- Y hoop stress, in megapascal (MPa)

Figure D.1 — Minimum required hydrostatic strength curves for PE-X