
**Non-destructive testing of welds —
Visual testing of fusion-welded joints**

*Contrôle non destructif des assemblages soudés — Contrôle visuel des
assemblages soudés par fusion*

STANDARDSISO.COM : Click to view the full PDF of ISO 17637:2003



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 17637:2003

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Test conditions and equipment	1
3 Personnel qualification	1
4 Visual testing	2
4.1 General	2
4.2 Visual testing of joint preparation	2
4.3 Visual testing during welding	2
4.4 Visual testing of the finished weld	2
4.5 Visual testing of repaired welds	3
5 Test records	4
Annex A (informative) Examples of testing equipment	5
Bibliography	10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 17637 was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 5, *Testing and inspection of welds*.

STANDARDSISO.COM : Click to view the full PDF of ISO 17637:2003

Non-destructive testing of welds — Visual testing of fusion-welded joints


1 Scope

This International Standard covers the visual testing of fusion welds in metallic materials. It may also be applied to visual testing of the joint prior to welding.

2 Test conditions and equipment

The illuminance at the surface shall be a minimum of 350 lx. However, 500 lx is recommended.

For direct inspection, the access shall be sufficient to place the eye within 600 mm of the surface to be examined and at an angle not less than 30° (see Figure 1).

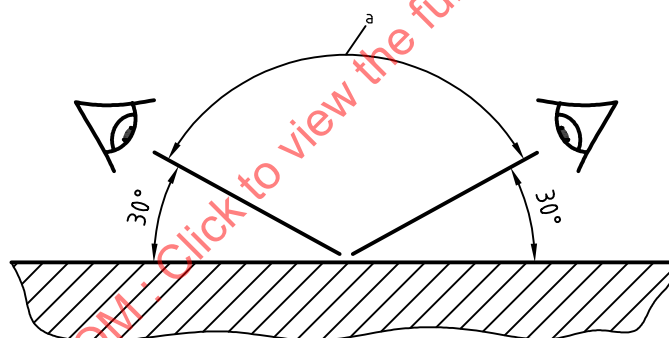

a Range

Figure 1 — Access for testing

Remote inspection using mirrors, boroscopes, fibre optic cables or cameras shall be considered when the access for testing in accordance with Figure 1 is not possible or when specified by an application standard.

An additional light source can be used to increase the contrast and relief between imperfections and the background.

Where the result of visual testing is inconclusive, the visual test should be supplemented by other non-destructive testing methods for surface inspections.

Examples of equipment used for visual testing are given in Annex A.

3 Personnel qualification

Visual testing of welds and the evaluation of results for final acceptance shall be performed by qualified and capable personnel. It is recommended that personnel be qualified in accordance with ISO 9712 or an equivalent standard at an appropriate level in the relevant industry sector.

4 Visual testing

4.1 General

This International Standard does not define the extent of visual testing. However, this should be determined in advance, e.g., by reference to an application or product standard.

The examiner shall have access to the necessary inspection and production documentation required.

Any visual testing prior to, during or after completion of the weld should be carried out while physical access is still possible. This may include the visual testing of surface treatments.

4.2 Visual testing of joint preparation

When visual testing is required prior to welding, the joint shall be examined to check that:

- a) the shape and dimensions of the weld preparation meet the requirements of the welding procedure specification;
- b) the fusion faces and adjacent surfaces are clean and any required surface treatment has been carried out in accordance with the application or product standard;
- c) the parts to be welded are correctly fixed in relation to each other according to drawings or instructions.

4.3 Visual testing during welding

When required, the weld shall be tested during the welding process to check that:

- a) each run or layer of weld metal is cleaned before it is covered by a further run, particular attention being paid to the junctions between the weld metal and the fusion face;
- b) there are no visible imperfections, e.g. cracks or cavities; if imperfections are observed, they shall be reported so that remedial action can be taken before the deposition of further weld metal;
- c) the transition between the runs and between the weld and the parent metal is so formed that satisfactory melting can be accomplished when welding the next run;
- d) the depth and shape of gouging is in accordance with the WPS or compared with the original groove shape in order to assure complete removal of the weld metal as specified;
- e) after any necessary repairs/remedial action, the weld conforms to the original requirements of the WPS.

4.4 Visual testing of the finished weld

4.4.1 General

The finished weld shall be examined to determine whether it meets the requirements of the application or product standard or other agreed acceptance criteria, e.g. ISO 5817 or ISO 10042. Finished welds shall at least be examined in accordance with the requirements given in 4.4.2 to 4.4.5.

4.4.2 Cleaning and dressing

The weld shall be examined to check that:

- a) all slag has been removed by manual or mechanical means in order to avoid imperfections being obscured;

- b) there are no tool impressions or blow marks;
- c) when weld dressing is required, overheating of the joint due to grinding is avoided and that grinding marks and an uneven finish are also avoided;
- d) for fillet welds and butt welds to be dressed flush, the joint merges smoothly with the parent metal without under flushing.

If imperfections (caused by dressing or otherwise) are observed, they shall be reported so that remedial action can be taken.

4.4.3 Profile and dimensions

The weld shall be examined to check that:

- a) the profile of the weld face and the height of any excess weld metal meet the requirements of the acceptance standard (see 4.4.1);
- b) the surface of the weld is regular: the pattern and the pitch of weave marks present an even and satisfactory visual appearance; the distance between the last layer and the parent metal or the position of runs has been measured where required by the WPS;
- c) the weld width is consistent over the whole of the joint and that it meets the requirements given in the weld drawing or acceptance standard (see 4.4.1); in the case of butt welds, the weld preparation shall be checked to ensure that it has been completely filled.

4.4.4 Weld root and surfaces

The visually accessible parts of the weld, i.e. the weld root for a single-sided butt weld and the weld surfaces, shall be examined for deviations from the acceptance standard (see 4.4.1).

The weld shall be examined to check that:

- a) in the case of single-sided butt welds, the penetration, root concavity and any burn-through or shrinkage grooves are within the limits specified in the acceptance standard over the whole of the joint;
- b) any undercut is within the requirements of the acceptance standard;
- c) any imperfections such as cracks or porosity, detected using optical aids when necessary, in the weld surface or heat affected zones comply with the appropriate acceptance criteria;
- d) any attachments temporarily welded to the object to facilitate production or assembly and which are prejudicial to the function of the object or the ability to examine it are removed so that the object is not damaged; the area where the attachment was fixed shall be checked to ensure freedom of cracks;
- e) any arc strikes are within the limits of the acceptance standard.

4.4.5 Post-weld heat treatment

Further testing may be required after post-weld heat treatment.

4.5 Visual testing of repaired welds

4.5.1 General

When welds fail to comply wholly or in part with the acceptance criteria and repair is necessary, the welded joint shall be examined in accordance with 4.5.2 and 4.5.3 prior to re-welding.

Every repaired weld shall be re-examined to the same requirements as the original weld.

4.5.2 Partially removed weld

The excavation shall be sufficiently deep and long to remove all imperfections. The excavation shall be tapered from the base of the cut to the surface of the weld metal at both the ends and sides of the cut. The width and profile of the cut shall be such that there is adequate access for re-welding.

4.5.3 Completely removed weld

When a defective weld has been completely removed, with or without the need for a new section to be inserted, the shape and dimensions of the weld preparation shall meet the specified requirements for the original weld.

5 Test records

When test records are required, at least the following information should be included in the report:

- a) name of the component manufacturer;
- b) name of the testing body, if different from a);
- c) identity of the object tested;
- d) material;
- e) type of joint;
- f) material thickness;
- g) welding process;
- h) acceptance criteria;
- i) imperfections exceeding the acceptance criteria and their location;
- j) the extent of testing with reference to drawings as appropriate;
- k) test devices used;
- l) result of testing with reference to acceptance criteria;
- m) name of tester and date of test.

Welds that have been tested and approved should be suitably marked or identified.

If a permanent visual record of an examined weld is required, photographs or accurate sketches or both should be made with any imperfections clearly indicated.

Annex A (informative)

Examples of testing equipment

A.1 The following is a list of equipment typically used for carrying out visual tests of welded joints:

- a) straight edge or measuring tape with a graduation of 1 mm or finer;
- b) vernier calliper in accordance with ISO 3599;
- c) feeler gauge with a sufficient number of feelers to measure dimensions between 0,1 mm and 3 mm in steps of 0,1 mm at most;
- d) radius gauge;
- e) magnifying lens with a magnification $\times 2$ to $\times 5$; the lens should preferably have a scale, see ISO 3058;
- f) lamps.

A.2 The following equipment may also be needed:

- a) profile measuring device with a wire diameter or width ≤ 1 mm, where each wire end is rounded;
- b) material for impression of welds, e.g. cold setting plastic or clay;
- c) for visual inspection of welds with limited accessibility, mirrors, endoscopes, boroscopes, fibre optics or TV-cameras may be used;
- d) other measurement devices e.g. specifically designed welding gauges, height/depth gauges, rulers or protractors.

A.3 Typical measurement devices and gauges are listed in detail in Table A.1.

NOTE These devices and gauges are included as examples of testing equipment. Some of the designs may be registered designs or the subject of patents.

Table A.1 — Measuring instruments and weld gauges — Measuring ranges and reading accuracy

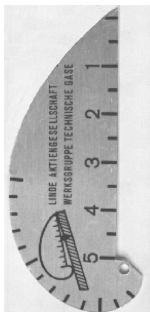
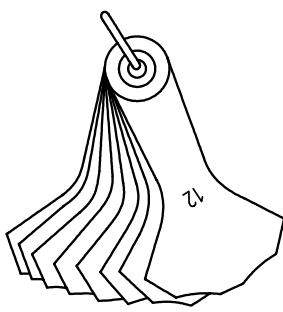
Weld gauge	Description	Type of weld				Measuring range mm	Reading accuracy mm	Included or fillet angle degrees	Permissible deviation of included or fillet angle
		Fillet weld		Butt weld					
		Flat weld	Concave weld	Convex weld					
	Simple weld gauge a) Measures fillet weld from 3 mm to 15 mm thickness. The gauge is placed by the curved part in the fusion faces so as to have three points of contact with the work piece and the fillet weld. b) Measures butt welds reinforcement with the straight part. Because the gauges consist of relatively soft aluminium, they wear out rapidly.	x	x	—	x	3 to 15	≈ 0,5	90	Small
	Set of welding gauges Measures fillet welds from 3 mm to 12 mm thickness; from 3 mm to 7 mm: graduations of 0,5 mm; above 8 mm, 10 mm and 12 mm. The gauge measures by using the principle of three-point contact.	x	x	—	—	3 to 12	according to fan part	90	None

Table A.1 (continued)

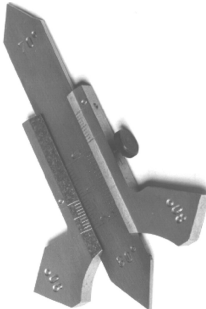
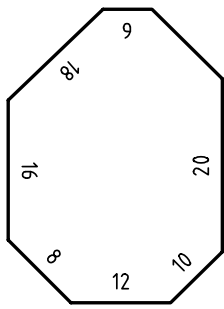
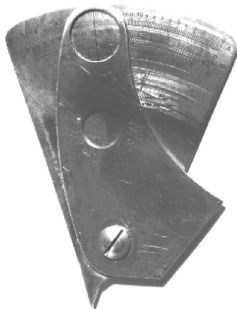
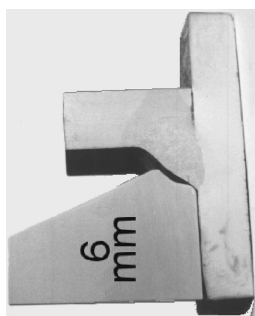
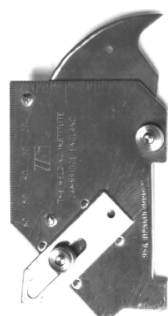
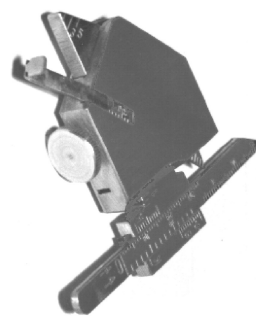
Weld gauge	Description	Type of weld				Measuring range mm	Reading accuracy mm	Included or fillet angle degrees	Permissible deviation of included or fillet angle
		Fillet weld			Butt weld				
		Flat weld	Concave weld	Convex weld					
	Weld gauge with Vernier Measures fillet welds; also reinforcement of butt welds can be determined. The legs of the gauge are so formed that included angles of 60°, 70°, 80° and 90° of V- and single-V butt weld with broad face can be measured. Slight deviations from these lead to significant errors.	x	x	—	x	0 to 20	0,1	90	None
	Self made weld gauge Measures 7 throat thicknesses of fillet welds with an included angle of 90°.	x	—	—	—	0 to 20	0,2	90	None
	Three-scale weld gauge Measures throat thickness and leg length. Can also measure weld reinforcement of butt welds. Easy to use. Also appropriate for asymmetric fillet welds.	x	x	x	x	0 to 15	0,1	90	Small

Table A.1 (continued)

Weld gauge	Description	Type of weld					Measuring range mm	Reading accuracy mm	Included or fillet angle degrees	Permissible deviation of included or fillet angle
		Fillet weld			Butt weld					
		Flat weld	Concave weld	Convex weld						
	Gauge for checking profile of fillet welds Checking the profile of one shape for one size of fillet welds. This type of gauge needs one model for each size of fillet weld.	—	—	—	—	—	—	—	—	—
	Multi-purpose gauge Measures angle of bevel, leg length of fillet weld, undercut, misalignment, throat thickness and weld reinforcement.	x	x	x	x	0 to 50	0,3	0 to 45 (angle of bevel)	None	
	Universal weld gauge Measurement tasks: — fillet welds: shape and dimensions. — butt welds: misalignment of plates, joint preparation (angle width), weld reinforcement, weld width, undercuts.	x	x	x	x	0 to 30	0,1	—	± 25 %	
	Gap gauge Measures the width of gaps.	—	—	—	x	0 to 6	0,1	—	—	—