
**Cryogenic vessels — Toughness
requirements for materials at cryogenic
temperature —**

**Part 2:
Temperatures between – 80 °C
and – 20 °C**

*Réipients cryogéniques — Exigences de ténacité pour les matériaux à
température cryogénique —*

Partie 2: Températures comprises entre – 80 °C et – 20 °C



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 21028-2:2004

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Requirements for steels with specified yield strength $\leq 460 \text{ N/mm}^2$	2
5 General test requirements	4
6 Welds	5
7 Requirements for aluminium and aluminium alloys, copper and copper alloys and austenitic stainless steels	5
Annex A (informative) Case proposal — Technical justification for temperature adjustment term	18
Bibliography	21

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 21028-2 was prepared by Technical Committee ISO/TC 220, *Cryogenic vessels*.

ISO 21028 consists of the following parts, under the general title *Cryogenic vessels — Toughness requirements for materials at cryogenic temperature*:

- *Part 1: Temperatures below – 80 °C*
- *Part 2: Temperatures between – 80 °C and – 20 °C*

Introduction

The use of materials at low temperatures entails special problems which have to be addressed. Consideration has to be given, in particular, to changes in mechanical characteristics, expansion and contraction phenomena and the thermal conduction of the various materials. The most important property to be considered is the material toughness at low temperature.

This part of ISO 21028 is based on European Standard EN 1252-2:2001.

STANDARDSISO.COM : Click to view the full PDF of ISO 21028-2:2004

Cryogenic vessels — Toughness requirements for materials at cryogenic temperature —

Part 2: Temperatures between – 80 °C and – 20 °C

1 Scope

This part of ISO 21028 specifies the toughness requirements of metallic materials for use at temperatures between – 20 °C and – 80 °C to ensure their suitability for cryogenic vessels. It is applicable to fine-grain and low-alloyed steels with specified yield strength $\leq 460 \text{ N/mm}^2$, aluminium and aluminium alloys, copper and copper alloys and austenitic stainless steels.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 148 (all parts), *Metallic materials — Charpy pendulum impact test*

ISO 15614-1, *Specification and qualification of welding procedures for metallic materials — Welding procedure test — Part 1: Arc and gas welding of steels and arc welding of nickel and nickel alloys*¹⁾

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

minimum metal temperature

T_M

lowest temperature defined for each of the conditions

- temperature during normal operation,
- temperature during start-up and shut down procedures,
- temperature which may occur during possible process upsets,
- temperature which may occur during pressure or leak testing, and
- ambient conditions

NOTE See also 3.2 and 3.3.

1) To be published.

3.2

temperature adjustment term

T_S

term relevant to the calculation of the **design reference temperature** T_R (3.3) and dependent on the pressure-induced principal membrane stress at the appropriate minimum metal temperature

3.3

design reference temperature

T_R

temperature used for determining the impact energy requirements, themselves determined by adding the **temperature adjustment term** T_S (3.2) to the **minimum metal temperature** T_M (3.1):

$$T_R = T_M + T_S$$

NOTE All applicable combinations of the temperatures T_M and T_S are to be considered, and the lowest possible T_R value used for the determination of the required material **impact test temperature** (3.4).

3.4

impact test temperature

T_{KV}

temperature at which the required impact energy has to be achieved

NOTE See Clause 5.

3.5

impact energy

KV

energy determined from Charpy V-notch tests performed in accordance with ISO 148.

3.6

reference thickness

e_B

thickness of a component used to relate the **design reference temperature** T_R (3.3) of the component with its required **impact test temperature** T_{KV} (3.4).

See Figures 1 to 5.

NOTE The reference thickness is based on the nominal thickness (including corrosion allowance) and shall be as defined in Table 6. For butt-welded components, it is the nominal wall thickness of the component at the edge of the weld preparation

4 Requirements for steels with specified yield strength $\leq 460 \text{ N/mm}^2$

4.1 General

This method, based on fracture mechanics, may be used to determine the requirements to avoid brittle fracture in C, CMn, fine-grain and low-alloy steels with a specified minimum yield strength $\leq 460 \text{ N/mm}^2$.

In this procedure, the impact test temperature T_{KV} is not equal to the design reference temperature T_R .

Parent material, welds and HAZ shall meet the impact energy (KV) and impact test temperature T_{KV} requirements given in Table 1 for design reference temperatures T_R and reference thicknesses. Values of T_R shall be calculated from T_M using the values of T_S given in 4.2.

For materials with a specified minimum yield strength $> 310 \text{ N/mm}^2$, the impact energy at T_{KV} given in Figure 1 and Figure 2 shall be 40 J.

Where 27 J is specified in the product standard, Figure 3 for the post-weld heat-treated condition applies.

For the as-welded case with minimum yield strength in the range $> 310 \text{ N/mm}^2$ and $\leq 360 \text{ N/mm}^2$, Figure 4 applies.

For minimum yield strength $> 360 \text{ N/mm}^2$, Figure 5 applies.

Table 1 — Impact energy requirements

Specified min. yield strength of base material N/mm ²	Required impact energy KV (on 10 mm × 10 mm test pieces) J	Figure defining required T_{KV}	
		Non-welded/ Post-weld heat-treated (PWHT)	As-welded (A-W)
< 310	27	1	2
$> 310, \leq 360$	40	1	2
	27	3	4
> 360	40	1	2
	27	3	5

4.2 Temperature adjustments

T_S is a temperature adjustment which may be used if the pressure-induced principal membrane stress does not exceed the percentage of the maximum allowable design stress or 50 N/mm^2 given in Table 2.

Table 2 — Temperature adjustments

Condition	Percentage of maximum allowable design stress			Membrane stress ^b
	$> 75 \% ; \leq 100 \%$	$\leq 75 \%$	$\leq 50 \%$	$\leq 50 \text{ N/mm}^2$
Non-welded, post-weld heat treated ^a	0 °C	+ 10 °C	+ 25 °C	+ 50 °C
As-welded and reference thickness $< 30 \text{ mm}$	0 °C	0 °C	0 °C	+ 40 °C

^a Also applicable for equipment where all nozzles and non-temporary welded attachments are first welded to vessel components and these sub-assemblies are post-weld heat-treated before being assembled into the equipment by butt-welding, but the main seams are not subsequently post-weld heat-treated.

^b In this case, the membrane stress should take account of internal and external pressure and dead weight.

4.3 Procedure for base material $< 10 \text{ mm}$ thick

Minimum T_R values are given in Table 3 which shall be used when the base material is less than 10 mm thick and the testing temperature T_{KV} is 20 °C . The impact energy requirements are as specified in the relevant materials standards.

If these materials are to be used below the T_R values given in Table 3, the testing shall be performed in accordance with the relevant curve for 10 mm in Figure 1 to Figure 5. The required energies for the sub-sized specimens are given in Table 4.

Table 3 — Minimum T_S values for base material < 10 mm thick and $T_{KV} = 20\text{ }^{\circ}\text{C}$

Thickness mm	As-welded (A-W)	Post-weld heat-treated (PWHT)
	$^{\circ}\text{C}$	
8	– 20	– 35
6	– 25	– 40
4	– 40	– 55
2	– 55	– 70

5 General test requirements

5.1 General

Where impact tests are required they shall be Charpy V-notched tests in accordance with ISO 148. The impact energy requirements shall be met in the base material, heat-affected zone and weld metal. The specimen position shall be in accordance with ISO 15614-1. From each sample three specimens shall be tested for each of the required positions and test temperatures. The mean value of the three specimens shall be at least equal to the impact energy requirement. Only one specimen may show a lower value, but this value shall not be less than 70 % of this requirement.

The required values for base material refer to the transverse direction. If transverse properties are not obtainable, the minimum impact energy requirements specified for transverse test pieces shall be multiplied by a factor of 1,5 for C, CMn, fine-grained and low-alloyed steels with a minimum specified yield strength $\leq 460\text{ N/mm}^2$. For other materials refer to the product standard.

5.2 Sub-sized specimens

If the base material is less than 10 mm thick the energy requirements shall be as given in Table 4.

Alternatively, where proportional reduced energy requirements are preferred, Table 5 shall be applied.

Table 4 — Impact requirements for sub-sized Charpy V-notched specimen if base material < 10 mm thick

Specimen geometry		
mm × mm		
10 × 10	10 × 7,5	10 × 5
27 J	22 J	19 J
40 J	32 J	28 J

5.3 Sub-sized specimens for components from which it is impossible to extract specimens of section size equal to reference thickness

There are cases of unusually shaped components and/or weld procedure and production plates where the Charpy V-notched specimen extracted is either < 10 mm or not representative of the section thickness.

In these cases sub-sized specimens shall be tested at lower impact test temperatures, in order to model the behaviour of a full thickness specimen, using temperature shifts in accordance with Table 5.

Impact tests should be performed on the maximum thickness which can be extracted from the component under consideration.

Table 5 — Equivalent impact energy requirements when sub-sized specimens extracted from thicker sections

Required impact energy KV J	Specimen geometry mm	Sub-sized specimen requirement		
		KV J	Specimen geometry mm × mm	Shift of impact test temperature °C
27	10 × 10	20	7,5 × 10	$T_{KV} - 5$
		14	5,0 × 10	$T_{KV} - 20$
40	10 × 10	30	7,5 × 10	$T_{KV} - 5$
		20	5,0 × 10	$T_{KV} - 20$
20	7,5 × 10	14	5,0 × 10	$T_{KV} - 15$
30	7,5 × 10	20	5,0 × 10	$T_{KV} - 15$

6 Welds


When materials are to be joined by welding, the choice of consumables and procedures (see ISO 15614-1) shall ensure that the required impact energy properties are achieved in weld regions and heat-affected zones, when tested in accordance with Clause 5.

The required impact energy shall be at least equal to the specified impact energy for the base metal.

7 Requirements for aluminium and aluminium alloys, copper and copper alloys and austenitic stainless steels


Toughness of aluminium and aluminium alloys, copper and copper alloys and austenitic stainless steels is inherently high enough at low temperature to render impact tests unnecessary.

Welds of austenitic stainless steels shall be impact tested if the material for the weld consumable shows that it has a ferrite content exceeding 10 %.

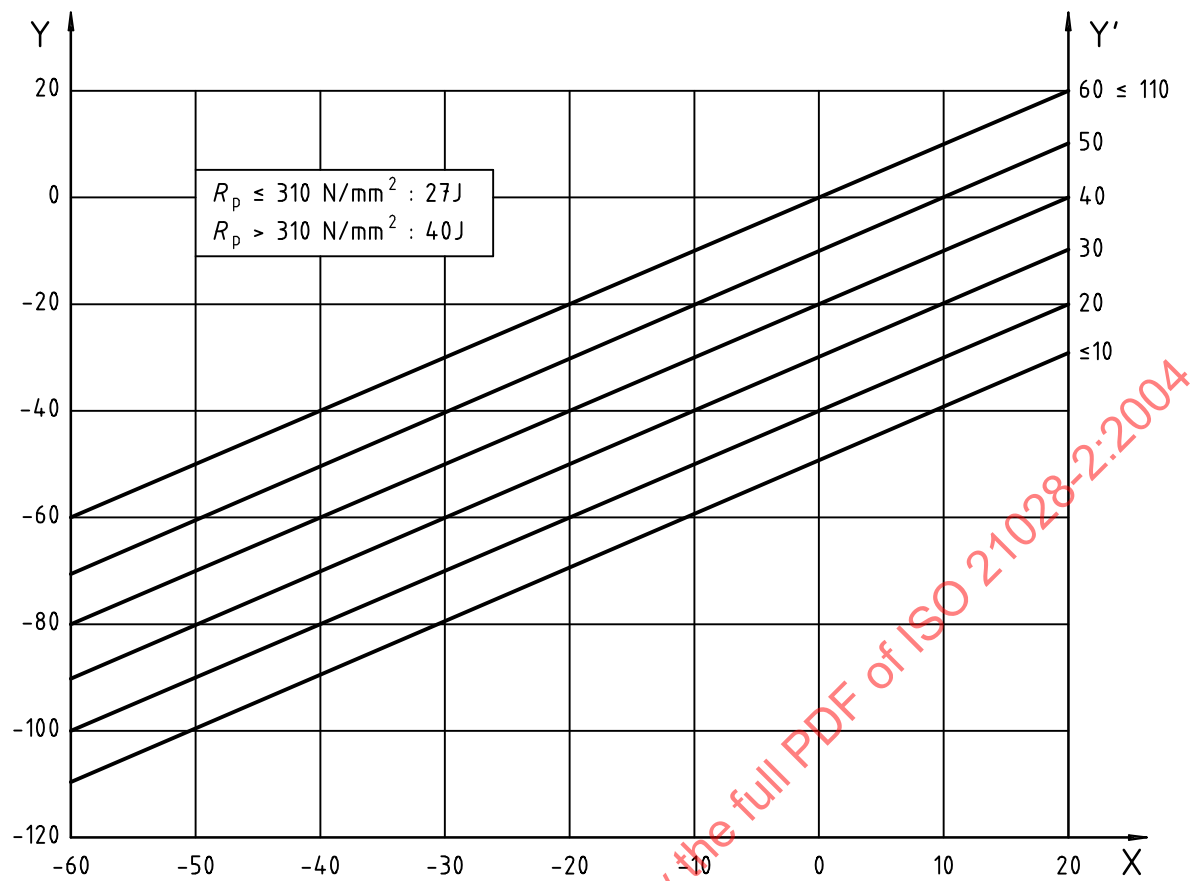


Key
Y T_R design reference temperature, °C
X T_{KV} impact test temperature, °C
Y' e_B reference thickness, mm
 R_p proof stress

Figure 1 — Design reference and impact test temperatures — Non-welded/Post-weld heat-treated condition

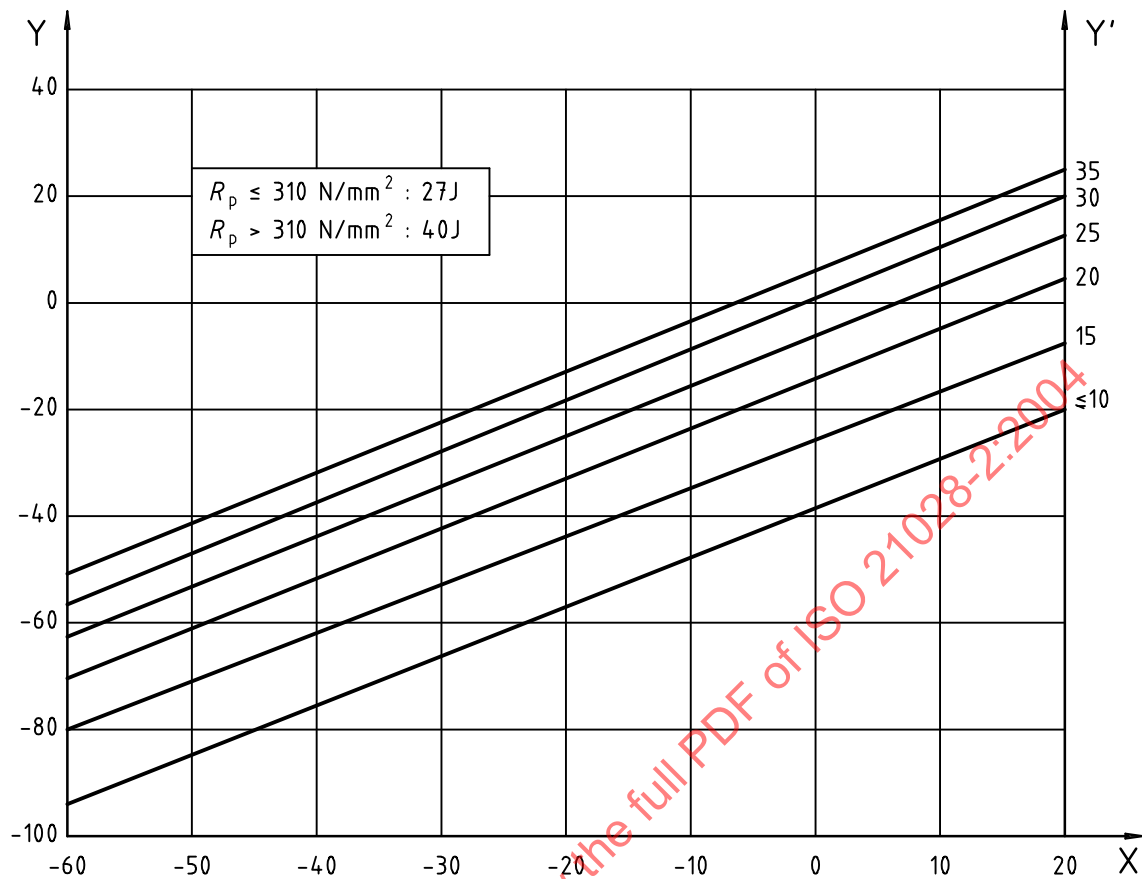**Key**


- Y T_R design reference temperature, °C
- X T_{KV} impact test temperature, °C
- Y' e_B reference thickness, mm
- R_p proof stress

Figure 2 — Design reference and impact test temperatures — As-welded condition

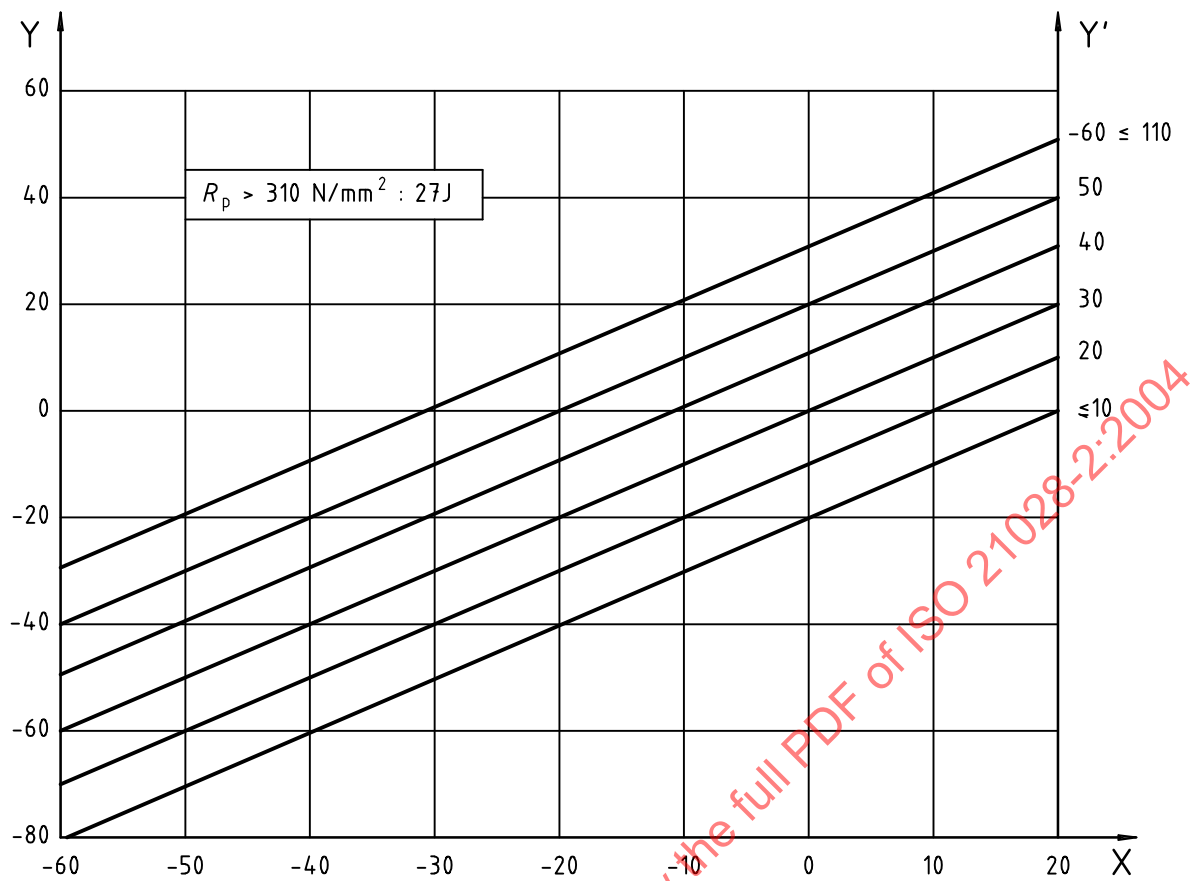


Key
Y T_R design reference temperature, °C
X T_{KV} impact test temperature, °C
Y' e_B reference thickness, mm
 R_p proof stress

Figure 3 — Design reference and impact test temperatures — Non-welded/Post-weld heat-treated condition

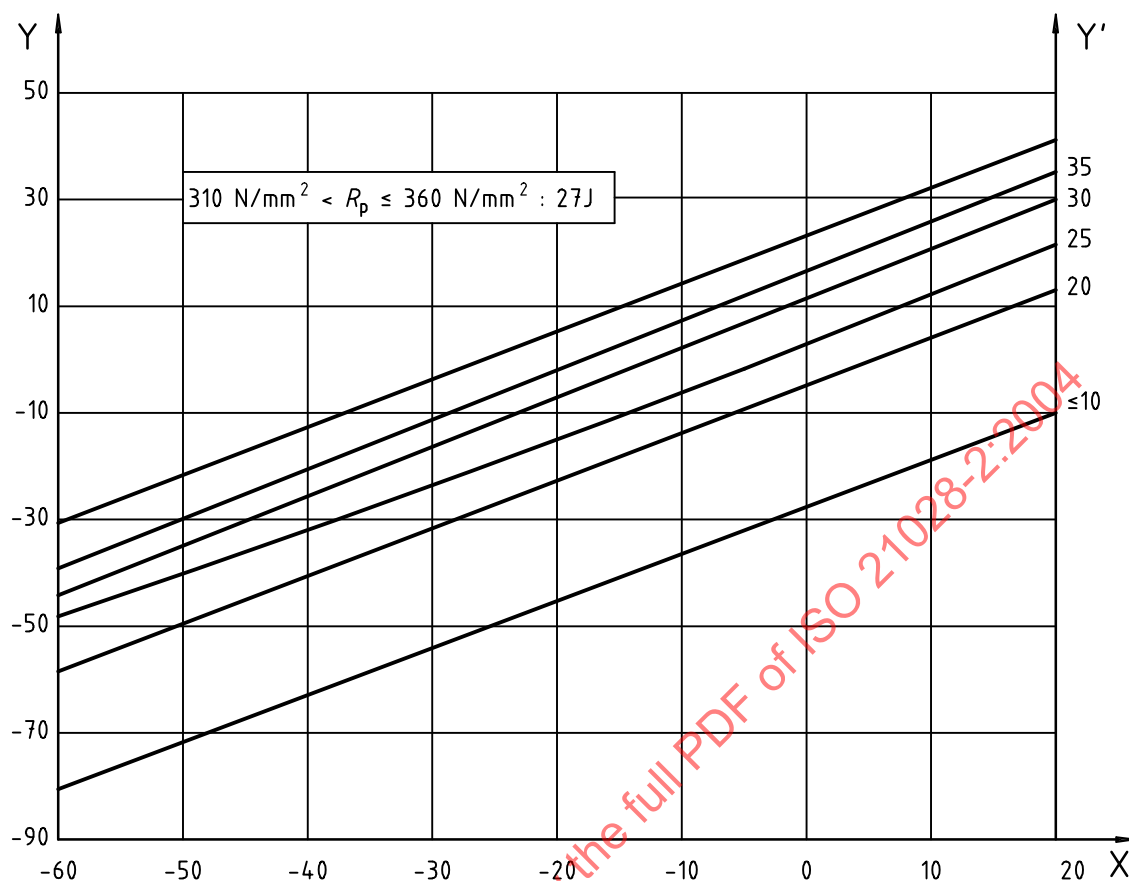**Key**

- Y T_R design reference temperature, °C
 X T_{KV} impact test temperature, °C
 Y' e_B reference thickness, mm
 R_p proof stress

Figure 4 — Design reference and impact test temperatures — As-welded condition

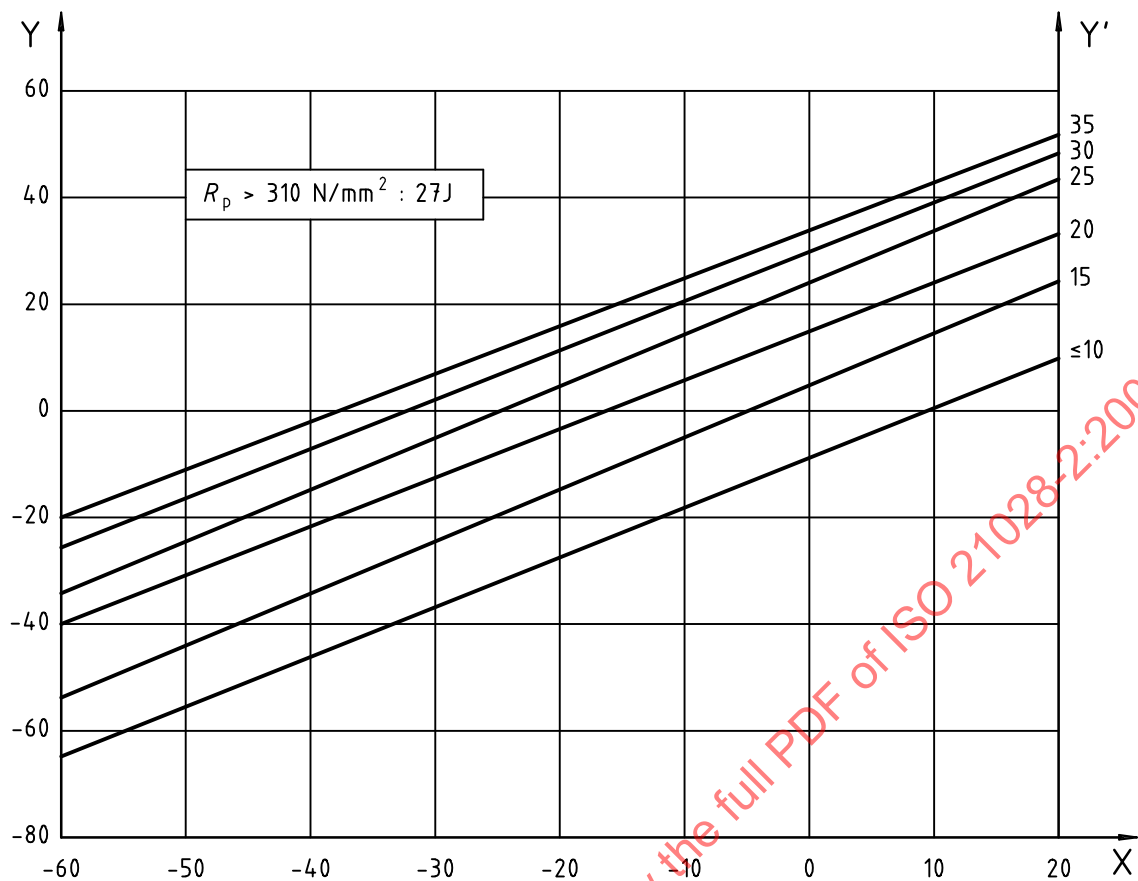

Key
Y T_R design reference temperature, °C
X T_{KV} impact test temperature, °C
Y' e_B reference thickness, mm
 R_p proof stress

Figure 5 — Design reference and impact test temperature — As-welded condition

Table 6 — Reference thicknesses

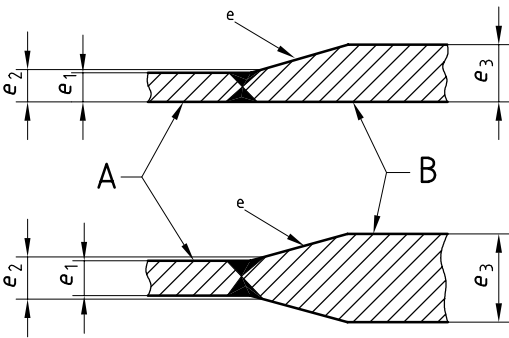
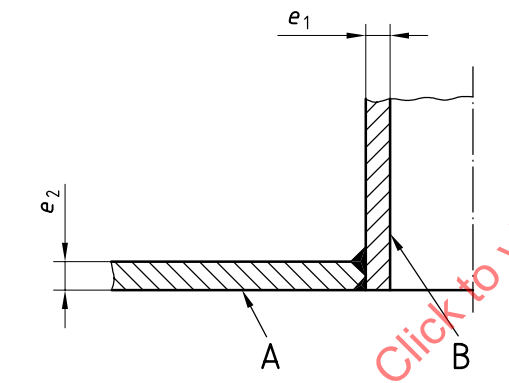
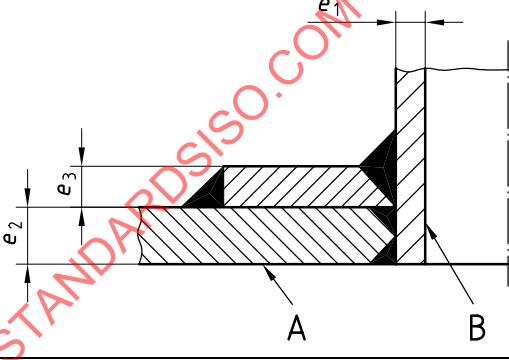
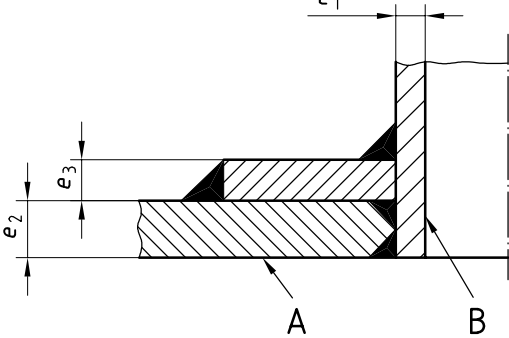
Construction detail	As-welded or Post-weld heat-treated	Reference thickness e_B (where $e_B = e_1, e_2, e_3$ or e_f)		
		Part A	Weld	Part B
Butt-welded components of unequal thickness 	A-W	e_1	e_2	e_2 check e_3 in Figure 1 or Figure 3 ^a
	PWHT	e_1	e_2	e_3
Branches and nozzles 	A-W	e_2	e_2	e_1
	PWHT	e_2	e_2	e_1
	A-W	e_2	e_2 or e_3 if thicker	e_1
	PWHT	e_2	e_2 or e_3 if thicker	e_1
	A-W	e_2	e_2 or e_3 if thicker	e_1
	PWHT	e_2	e_2 or e_3 if thicker	e_1

Table 6 (continued)

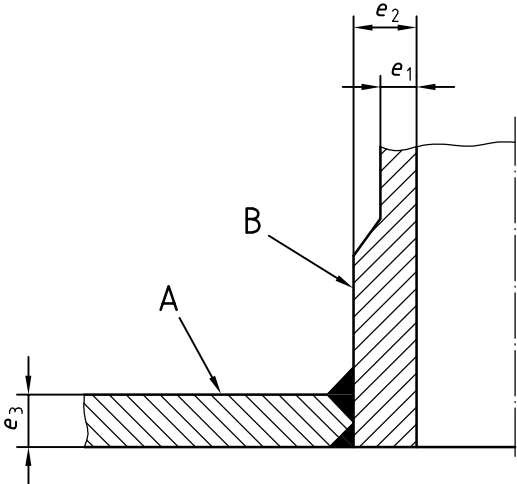
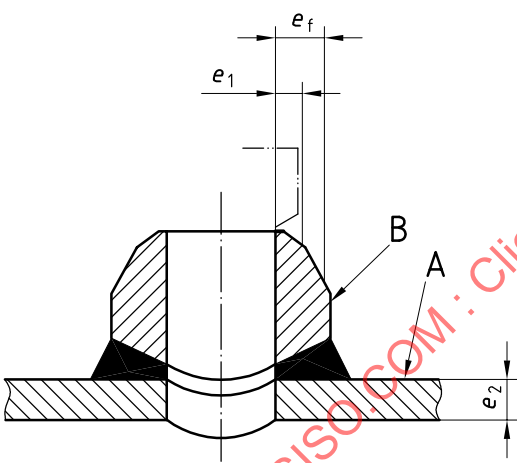
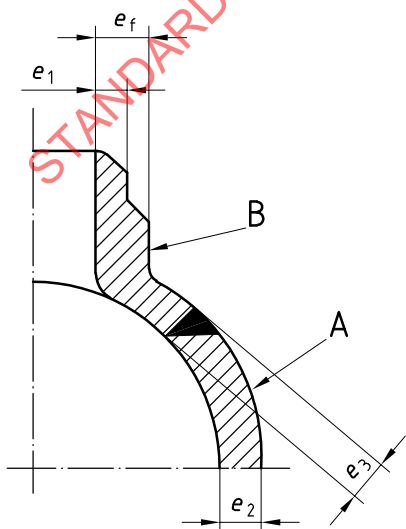
Construction detail	As-welded or Post-weld heat-treated	Reference thickness e_B (where $e_B = e_1, e_2, e_3$ or e_f)		
		Part A	Weld	Part B
	A-W	e_3	e_2 or e_3 if thicker	e_2
	PWHT	e_3	e_2 or e_3 if thicker	e_2
	A-W	e_2	e_2	e_1 or $e e_f / 4$ if thicker
	PWHT	e_2	e_2	e_1^b or $e e_f / 4$ if thicker if necessary, check e_1 in Figure 2 or 4
	A-W	e_2	e_3	e_3 or $e e_f / 4$ if thicker
	PWHT	e_2	e_3	e_3^c or $e e_f / 4$ if thicker if necessary, check e_1 in Figure 2 or 4

Table 6 (continued)

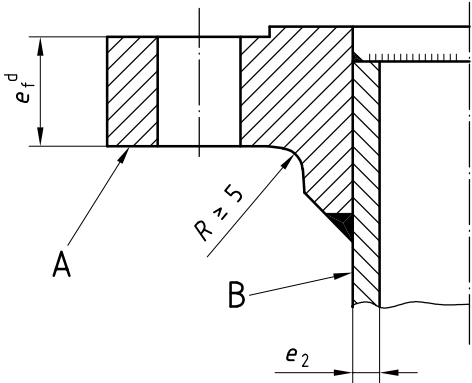
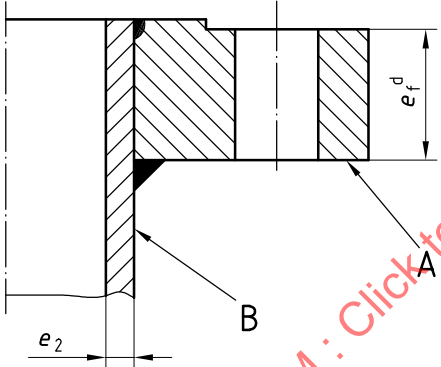
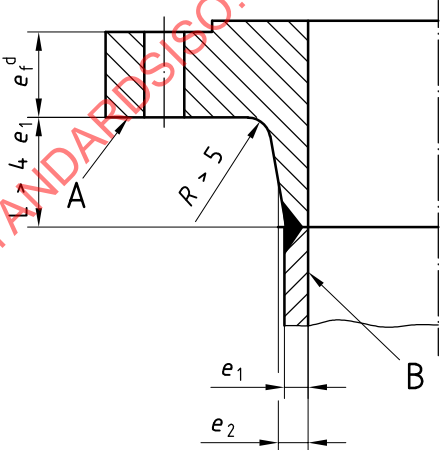
Construction detail	As-welded or Post-weld heat-treated	Reference thickness e_B (where $e_B = e_1, e_2, e_3$ or e_f)		
		Part A	Weld	Part B
Slip-on and plate flanges 	A-W	$e_f/4$	e_2	e_2
	PWHT	$e_f/4$	e_2	e_2
	A-W	$e_f/4$	e_2	e_2
	PWHT	$e_f/4$	e_2	e_2
Forged or cast welding neck flanges 	A-W	e_2^c check $e_f/4$ in Figure 1 or 3	e_2	e_1
	PWHT	e_2 or $e_f/4$ if thicker	e_2	e_1

Table 6 (continued)

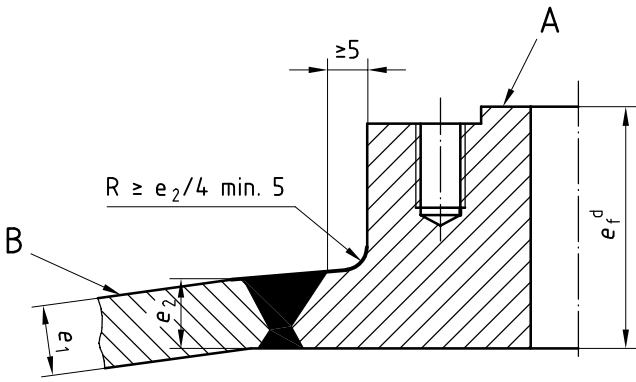
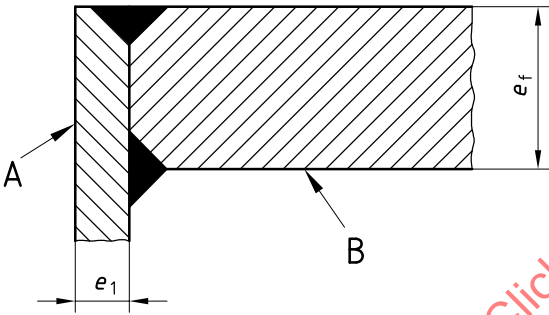
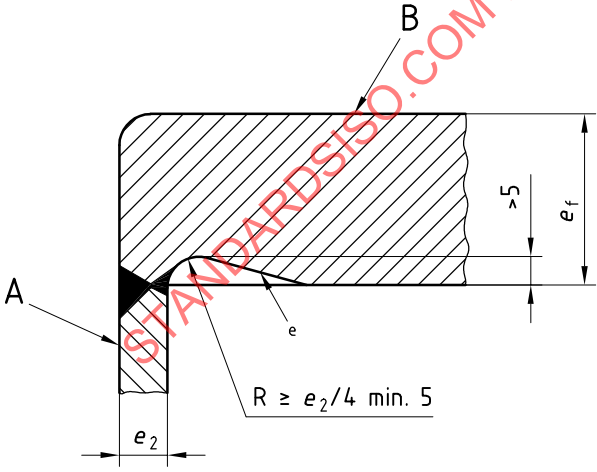
Construction detail	As-welded or Post-weld heat-treated	Reference thickness e_B (where $e_B = e_1, e_2, e_3$ or e_f)		
		Part A	Weld	Part B
Pad-type flanges 	A-W	e_2^c check $e_f/4$ in Figure 1 or 3	e_2	e_1
	PWHT	e_2 or $e_f/4$ if thicker	e_2	e_1
Flat ends 	A-W	e_1	e_1	$e_f/4$ or e_1 if thicker
	PWHT	e_1	e_1	$e_f/4$ or e_1 if thicker
	A-W	e_2	e_2	e_2^c check $e_f/4$ in Figure 1 or 3
	PWHT	e_2	e_2	$e_f/4$ or e_2 if thicker

Table 6 (continued)

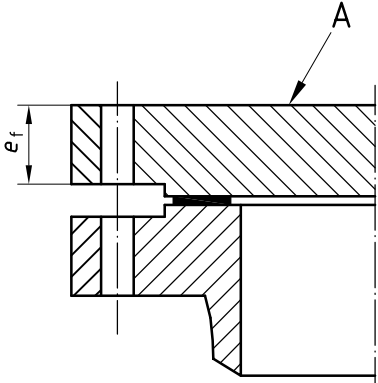
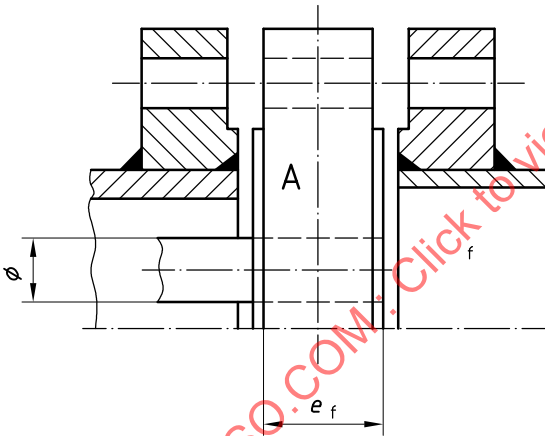
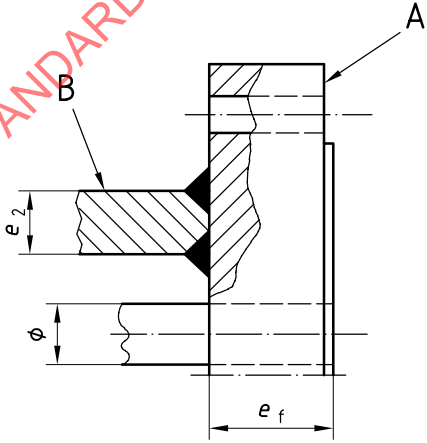
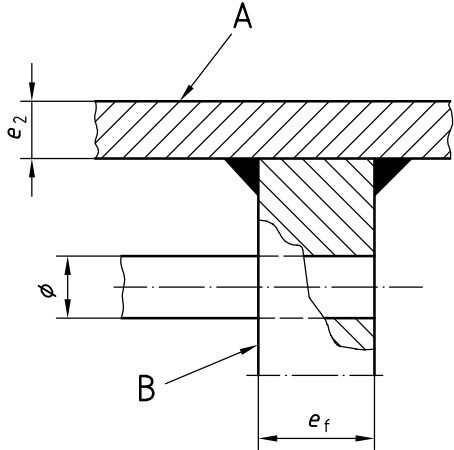
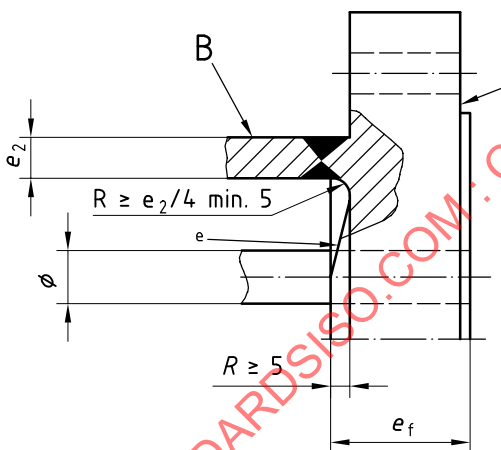
Construction detail	As-welded or Post-weld heat-treated	Reference thickness e_B (where $e_B = e_1, e_2, e_3$ or e_f)		
		Part A	Weld	Part B
Covers and blind flanges 	A-W	$e_f/4$	—	—
	PWHT	$e_f/4$	—	—
Tube plates 	A-W	N/A	N/A	N/A
	PWHT	$e_f/4$	N/A	N/A
	A-W	$e_f/4$ or e_2 if thicker	e_2	e_2
	PWHT	$e_f/4$ or e_2 if thicker	e_2	e_2

Table 6 (continued)

Construction detail	As-welded or Post-weld heat-treated	Reference thickness e_B (where $e_B = e_1, e_2, e_3$ or e_f)		
		Part A	Weld	Part B
<p>Welded into shell/channel</p>  <p>Preferably not to be used</p>	A-W	$e_f/4$ or e_2 if thicker	e_2	e_2
	PWHT	$e_f/4$ or e_2 if thicker	e_2	e_2
<p>Forged tube plate with stubs</p> 	A-W	e_2^c check $e_f/4$ in Figure 1 or 3	e_2	e_2
	PWHT	$e_f/4$ or e_2 if thicker	e_2	e_2