

---

---

**Wrought aluminium and aluminium  
alloys — Sheets, strips and plates —**

**Part 4:  
Sheets and plates: Tolerances on  
shape and dimensions**

*Aluminium et alliages d'aluminium corroyés — Tôles, bandes et tôles  
épaisses —*

*Partie 4: Tôles et tôles épaisses: Tolérances sur forme et dimensions*



STANDARDSISO.COM : Click to view the full PDF of ISO 6361-4:2014



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword .....	iv
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Dimensional tolerances</b> .....	<b>1</b>
3.1 Thickness .....	1
3.2 Width .....	5
3.3 Length .....	6
<b>4 Shape tolerances</b> .....	<b>7</b>
4.1 Lateral curvature .....	7
4.2 Flatness tolerances .....	7
4.3 Squareness tolerances .....	10
<b>Bibliography</b> .....	<b>12</b>

STANDARDSISO.COM : Click to view the full PDF of ISO 6361-4:2014

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 79, *Light metals and their alloys*, Subcommittee SC 6, *Wrought aluminium and aluminium alloys*.

This third edition cancels and replaces the second edition (ISO 6361-4:2011), which has been technically revised.

ISO 6361 consists of the following parts, under the general title *Wrought aluminium and aluminium alloys — Sheets, strips and plates*:

- *Part 1: Technical conditions for inspection and delivery*
- *Part 2: Mechanical properties*
- *Part 3: Strips: Tolerances on shape and dimensions*
- *Part 4: Sheets and plates: Tolerances on shape and dimensions*
- *Part 5: Chemical composition*

# Wrought aluminium and aluminium alloys — Sheets, strips and plates —

## Part 4: Sheets and plates: Tolerances on shape and dimensions

### 1 Scope

This part of ISO 6361 specifies the tolerances on shape and dimensions for wrought aluminium and aluminium alloy sheet and plate by hot-rolling or cold-rolling for general engineering applications.

It applies to products with a thickness over 0,15 mm up to and including 203 mm.

It does not apply to semi-finished rolled products in coiled form to be subjected to further rolling (reroll stock) or to special products, such as those that are corrugated or embossed.

Technical conditions for inspection and delivery of products covered by this part of ISO 6361 are specified in ISO 6361-1.

### 2 Normative references

No normative references cited in this document.

### 3 Dimensional tolerances

#### 3.1 Thickness

Thickness tolerances for a cold-rolled product are specified in [Table 1](#) and [Table 2](#).

Thickness tolerances for a hot-rolled product are specified in [Table 3](#) and [Table 4](#).

When the tolerance is specified as either all plus or minus side, the value in [Table 1](#), [Table 2](#), [Table 3](#), or [Table 4](#) shall be doubled.

Tolerances for the products exceeding the range of specified thickness and width shall be agreed upon between the purchaser and the supplier.

**Table 1 — Thickness tolerances for cold-rolled product**

Dimensions in millimetres

Specified thickness		Alloy number 1050, 1050A, 1070, 1070A, 1080, 1080A, 1085, 1100, 1100A, 1200, 1230A, 3003, 3103, 3203, 3005, 3105, 4006, 4007, 4015, 5005, 5010, 5110A, 5050, 8011A, 8021, 8079					
		Specified width					
Over	Up to and including	Up to and including 450	Over 450, up to and including 900	Over 900, up to and including 1 400	Over 1 400, up to and including 1 800	Over 1 800, up to and including 2 300	Over 2 300, up to and including 2 600
		Tolerance					
≥0,15	0,20	±0,03	±0,03	±0,05			

Table 1 (continued)

Specified thickness		Alloy number 1050, 1050A, 1070, 1070A, 1080, 1080A, 1085, 1100, 1100A, 1200, 1230A, 3003, 3103, 3203, 3005, 3105, 4006, 4007, 4015, 5005, 5010, 5110A, 5050, 8011A, 8021, 8079					
		Specified width					
Over	Up to and including	Up to and including 450	Over 450, up to and including 900	Over 900, up to and including 1 400	Over 1 400, up to and including 1 800	Over 1 800, up to and including 2 300	Over 2 300, up to and including 2 600
		Tolerance					
0,20	0,25	±0,03	±0,04	±0,05			
0,25	0,45	±0,04	±0,04	±0,05	±0,06		
0,45	0,70	±0,04	±0,05	±0,06	±0,08		
0,70	0,90	±0,05	±0,05	±0,06	±0,09	±0,13	
0,90	1,1	±0,05	±0,06	±0,08	±0,10	±0,13	
1,1	1,7	±0,06	±0,08	±0,10	±0,13	±0,15	
1,7	1,9	±0,06	±0,08	±0,10	±0,15	±0,20	
1,9	2,4	±0,08	±0,08	±0,10	±0,15	±0,20	
2,4	2,7	±0,09	±0,10	±0,13	±0,18	±0,23	
2,7	3,6	±0,11	±0,11	±0,13	±0,18	±0,23	±0,25
3,6	4,5	±0,15	±0,15	±0,20	±0,23	±0,28	±0,30
4,5	5,0	±0,18	±0,18	±0,23	±0,28	±0,33	±0,38
5,0	6,5	±0,23	±0,23	±0,28	±0,33	±0,38	±0,43
6,5	8,0	±0,33	±0,33	±0,33	±0,38	±0,43	±0,51
8,0	11	±0,48	±0,48	±0,48	±0,48	±0,58	±0,66
11	16	±0,64	±0,64	±0,64	±0,64	±0,76	±0,89

Table 2 — Thickness tolerances for cold-rolled product

Dimensions in millimetres

Specified thickness		Alloy number 2014, 2014A, 2017, 2017A, 2618A, 2219, 2024, 2124, 3004, 3104, 5021, 5026, 5040, 5042, 5049, 5449, 5251, 5052, 5154, 5154A, 5254, 5454, 5754, 5456, 5059, 5070, 5082, 5182, 5083, 5383, 5086, 6016, 6025, 6061, 6082, 7204, 7010, 7020, 7021, 7022, 7050, 7075, 7475, 7178											
		Specified width											
Over	Up to and including	Up to and including 450	Over 450, up to and including 900	Over 900, up to and including 1 200	Over 1 200, up to and including 1 400	Over 1 400, up to and including 1 500	Over 1 500, up to and including 1 700	Over 1 700, up to and including 1 800	Over 1 800, up to and including 2 000	Over 2 000, up to and including 2 100	Over 2 100, up to and including 2 300	Over 2 300, up to and including 2 400	Over 2 400, up to and including 2 600
		Tolerance											
≥0,20	0,25	±0,03	±0,04	±0,06	±0,06								
0,25	0,45	±0,04	±0,04	±0,06	±0,09								
0,45	0,70	±0,04	±0,05	±0,06	±0,09	±0,10	±0,10	±0,10					
0,70	0,90	±0,05	±0,05	±0,06	±0,10	±0,13	±0,13	±0,13	±0,15				
0,90	1,1	±0,05	±0,06	±0,08	±0,10	±0,13	±0,13	±0,13	±0,15				
1,1	1,7	±0,06	±0,08	±0,10	±0,13	±0,15	±0,15	±0,15	±0,18				
1,7	1,9	±0,08	±0,08	±0,10	±0,13	±0,15	±0,15	±0,15	±0,18				
1,9	2,4	±0,09	±0,09	±0,10	±0,13	±0,15	±0,15	±0,15	±0,18	±0,18	±0,30		

Table 2 (continued)

Specified thickness		Alloy number											
		2014, 2014A, 2017, 2017A, 2618A, 2219, 2024, 2124, 3004, 3104, 5021, 5026, 5040, 5042, 5049, 5449, 5251, 5052, 5154, 5154A, 5254, 5454, 5754, 5456, 5059, 5070, 5082, 5182, 5083, 5383, 5086, 6016, 6025, 6061, 6082, 7204, 7010, 7020, 7021, 7022, 7050, 7075, 7475, 7178											
Over	Up to and including	Specified width											
		Up to and including 450	Over 450, up to and including 900	Over 900, up to and including 1 200	Over 1 200, up to and including 1 400	Over 1 400, up to and including 1 500	Over 1 500, up to and including 1 700	Over 1 700, up to and including 1 800	Over 1 800, up to and including 2 000	Over 2 000, up to and including 2 100	Over 2 100, up to and including 2 300	Over 2 300, up to and including 2 400	Over 2 400, up to and including 2 600
		Tolerance											
2,4	2,7	±0,10	±0,10	±0,13	±0,13	±0,18	±0,18	±0,18	±0,20	±0,20	±0,41		
2,7	3,2	±0,11	±0,11	±0,13	±0,13	±0,18	±0,18	±0,18	±0,20	±0,20	±0,41	±0,46	±0,51
3,2	3,6	±0,11	±0,11	±0,13	±0,13	±0,18	±0,25	±0,30	±0,33	±0,36	±0,41	±0,46	±0,51
3,6	4,5	±0,15	±0,15	±0,20	±0,20	±0,23	±0,30	±0,36	±0,38	±0,41	±0,43	±0,48	±0,58
4,5	5,0	±0,18	±0,18	±0,25	±0,25	±0,28	±0,36	±0,41	±0,43	±0,43	±0,43	±0,56	±0,66
5,0	6,5	±0,23	±0,23	±0,28	±0,28	±0,33	±0,41	±0,46	±0,46	±0,46	±0,46	±0,61	±0,71
6,5	8,0	±0,33	±0,33	±0,33	±0,33	±0,38	±0,46	±0,51	±0,51	±0,51	±0,51	±0,64	±0,76
8,0	11	±0,48	±0,48	±0,48	±0,48	±0,51	±0,51	±0,58	±0,58	±0,64	±0,64	±0,66	±0,84
11	16	±0,64	±0,64	±0,64	±0,64	±0,64	±0,64	±0,64	±0,76	±0,76	±0,76	±0,89	±0,89

Table 3 — Thickness tolerances for hot-rolled product

Dimensions in millimetres

Specified thickness		Alloy number					
		1050, 1050A, 1070, 1070A, 1080, 1080A, 1085, 1100, 1100A, 1200, 1230A, 3003, 3103, 3203, 3005, 3105, 4006, 4007, 4015, 5005, 5010, 5110A, 5050, 8011A					
Over	Up to and including	Specified width					
		Up to and including 900	Over 900, up to and including 1 400	Over 1 400, up to and including 1 800	Over 1 800, up to and including 2 300	Over 2 300, up to and including 2 600	Over 2 600, up to and including 3 400
		Tolerance					
≥4	5	±0,25	±0,30	±0,35	±0,40		
5	6	±0,30	±0,40	±0,45	±0,50		
6	8	±0,45	±0,45	±0,55	±0,65	±0,75	±0,85
8	11	±0,55	±0,55	±0,65	±0,75	±0,85	±0,95
11	16	±0,65	±0,65	±0,75	±0,85	±0,95	±1,0
16	22	±0,80	±0,80	±0,80	±0,90	±1,1	±1,1
22	29	±0,90	±0,90	±0,90	±1,1	±1,4	±1,4
29	35	±1,0	±1,0	±1,0	±1,3	±1,7	±1,7
35	40	±1,1	±1,1	±1,1	±1,5	±1,9	±1,9
40	50	±1,3	±1,3	±1,3	±1,8	±2,2	±2,2
50	55	±1,5	±1,5	±1,5	±2,0	±2,5	±2,5

NOTE This specification shall be applied to the products of temper grade H112 and those finished by the hot-rolled condition.

**Table 3 (continued)**

Specified thickness		Alloy number					
		1050, 1050A, 1070, 1070A, 1080, 1080A, 1085, 1100, 1100A, 1200, 1230A, 3003, 3103, 3203, 3005, 3105, 4006, 4007, 4015, 5005, 5010, 5110A, 5050, 8011A					
Over	Up to and including	Specified width					
		Up to and including 900	Over 900, up to and including 1 400	Over 1 400, up to and including 1 800	Over 1 800, up to and including 2 300	Over 2 300, up to and including 2 600	Over 2 600, up to and including 3 400
		Tolerance					
55	70	±1,9	±1,9	±1,9	±2,5	±3,2	±3,2
70	75	±2,3	±2,3	±2,3	±3,0	±3,8	±3,8
75	100	±2,8	±2,8	±2,8	±3,6	±4,1	±4,1
100	150	±3,2	±3,2	±3,8	±4,1		
150	203	±4,1	±4,1	±4,1	±4,1		

NOTE This specification shall be applied to the products of temper grade H112 and those finished by the hot-rolled condition.

**Table 4 — Thickness tolerances for hot-rolled product**

Dimensions in millimetres

Specified thickness		Alloy number					
		2014, 2014A, 2017, 2017A, 2618A, 2219, 2024, 2124, 3004, 3104, 5021, 5026, 5040, 5042, 5049, 5449, 5251, 5052, 5154, 5154A, 5254, 5454, 5754, 5456, 5059, 5070, 5082, 5182, 5083, 5383, 5086, 6016, 6025, 6061, 6082, 7204, 7010, 7020, 7021, 7022, 7050, 7075, 7475, 7178					
Over	Up to and including	Specified width					
		Up to and including 900	Over 900, up to and including 1 400	Over 1 400, up to and including 1 800	Over 1 800, up to and including 2 300	Over 2 300, up to and including 2 600	Over 2 600, up to and including 3 400
		Tolerance					
≥4	5	±0,30	±0,35	±0,50	±0,60		
5	6	±0,40	±0,45	±0,55	±0,65		
6	8	±0,50	±0,50	±0,60	±0,70	±0,80	±0,90
8	11	±0,60	±0,60	±0,70	±0,80	±0,90	±1,0
11	16	±0,70	±0,70	±0,80	±0,90	±1,0	±1,1
16	22	±0,80	±0,80	±0,80	±0,90	±1,1	±1,1
22	29	±0,90	±0,90	±0,90	±1,1	±1,4	±1,4
29	35	±1,0	±1,0	±1,0	±1,3	±1,7	±1,7
35	40	±1,1	±1,1	±1,1	±1,5	±1,9	±1,9
40	50	±1,3	±1,3	±1,3	±1,8	±2,2	±2,2
50	55	±1,5	±1,5	±1,5	±2,0	±2,5	±2,5
55	70	±1,9	±1,9	±1,9	±2,5	±3,2	±3,2
70	75	±2,3	±2,3	±2,3	±3,0	±3,8	±3,8

NOTE This specification shall be applied to the products of temper grade H112 and those finished by the hot-rolled condition.

Table 4 (continued)

Specified thickness		Alloy number 2014, 2014A, 2017, 2017A, 2618A, 2219, 2024, 2124, 3004, 3104, 5021, 5026, 5040, 5042, 5049, 5449, 5251, 5052, 5154, 5154A, 5254, 5454, 5754, 5456, 5059, 5070, 5082, 5182, 5083, 5383, 5086, 6016, 6025, 6061, 6082, 7204, 7010, 7020, 7021, 7022, 7050, 7075, 7475, 7178					
		Specified width					
Over	Up to and including	Up to and including 900	Over 900, up to and including 1 400	Over 1 400, up to and including 1 800	Over 1 800, up to and including 2 300	Over 2 300, up to and including 2 600	Over 2 600, up to and including 3 400
		Tolerance					
75	100	±2,8	±2,8	±2,8	±3,6	±4,1	±4,1
100	150	±3,2	±3,2	±3,6	±4,1	±4,1	
150	203	±4,1	±4,1	±4,1	±4,1	±4,1	

NOTE This specification shall be applied to the products of temper grade H112 and those finished by the hot-rolled condition.

### 3.2 Width

Width tolerances for shared sheet and plate are specified in [Table 5](#).

Width tolerances for sawed sheet and plate are specified in [Table 6](#).

Width is measured at room temperature during cutting. The allowable maximum deviation shall be 0,23 mm per 1 000 mm in width, by a temperature difference of 10 °C against the reference temperature of 20 °C.

When the width tolerance for the product with a thickness of up to and including 6,5 mm is specified as either all plus or minus side, the value in [Table 5](#) or [Table 6](#) shall be doubled.

Tolerances for the products exceeding the range of specified thickness and width shall be agreed upon between the purchaser and the supplier.

Table 5 — Width tolerance for sheared sheet and plate

Dimensions in millimetres

Specified thickness		Specified width			
Over	Up to and including	Up to and including 150	Over 150, up to and including 600	Over 600, up to and including 2 500	Over 2 500, up to and including 3 500
		Tolerance			
≥0,15	3,2	±2	±3	±3	±4
3,2	6,5	±3	±3	±3	±5
6,5	16	+7 0	+8 0	+10 0	+11 0

**Table 6 — Width tolerances for sawed sheet and plate**

Dimensions in millimetres

Specified thickness		Specified width			
Over	Up to and including	Up to and including 1 000	Over 1 000, up to and including 2 000	Over 2 000, up to and including 3 000	Over 3 000, up to and including 3 500
<b>Tolerance</b>					
≥2,0	6,5	±3	±3	±5	±7
6,5	203	+7 0	+8 0	+10 0	+13 0

**3.3 Length**

Length tolerances for sheared sheet and plate are specified in [Table 7](#).

Length tolerances for sawed sheet and plate are specified in [Table 8](#).

Length is measured at room temperature during cutting. The allowable maximum deviation shall be 0,23 mm per 1 000 mm in length, by a temperature difference of 10 °C against the reference temperature of 20 °C.

When the width tolerance for the product with a thickness of up to and including 6,5 mm is specified as either all plus or minus side, the value in [Table 7](#) or [Table 8](#) shall be doubled.

Tolerances for the products exceeding the range of specified thickness and width shall be agreed upon between the purchaser and the supplier.

**Table 7 — Length tolerances for sheared sheet and plate**

Dimensions in millimetres

Specified thickness		Specified length					
Over	Up to and including	Up to and including 750	Over 750, up to and including 1 500	Over 1 500, up to and including 3 000	Over 3 000, up to and including 6 000	Over 6 000, up to and including 9 000	Over 9 000, up to and including 10 000
<b>Tolerance</b>							
≥0,15	3,2	±2	±3	±3	±4	±5	±6
3,2	6,5	±3	±3	±3	±4	±6	±7
6,5	16	+7 0	+10 0	+11 0	+13 0	+14 0	+16 0

**Table 8 — Length tolerances for sawed sheet and plate**


Dimensions in millimetres

Specified thickness		Specified length					
Over	Up to and including	Up to and including 750	Over 750, up to and including 1 500	Over 1 500, up to and including 3 000	Over 3 000, up to and including 6 000	Over 6 000, up to and including 9 000	Over 9 000, up to and including 10 000
<b>Tolerance</b>							
≥2,0	6,5	±3	±3	±5	±7	±7	±8
6,5	203	+7 0	+8 0	+10 0	+13 0	+14 0	+16 0

## 4 Shape tolerances

### 4.1 Lateral curvature

Lateral curvature is the depth of the arc over the whole length as shown in [Figure 1](#).

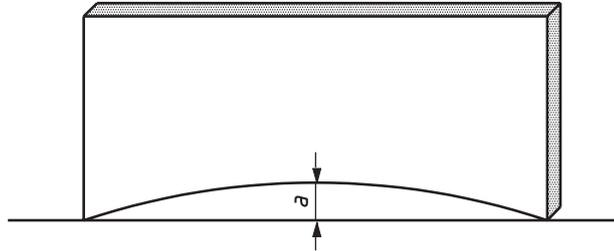

#### Key

*a* maximum value

**Figure 1 — Lateral curvature of sheet and plate**

When tested with the sheet resting on a flat surface against a straight edge, the lateral curvature shall not exceed the appropriate value given in [Table 9](#).

The maximum value for the products exceeding the range of specified thickness, width, and length shall be agreed upon between the purchaser and the supplier.

**Table 9 — Lateral curvature tolerances**

Dimensions in millimetres

Specified thickness		Specified width		Specified length						
Over	Up to and including	Over	Up to and including	Up to and including 1 500	Over 1 500, up to and including 2 300	Over 2 300, up to and including 3 000	Over 3 000, up to and including 3 800	Over 3 800, up to and including 4 500	Over 4 500, up to and including 5 500	Over 5 500, up to and including 6 000
Maximum values										
≥0,15	3,2		100	6	14	25	39	57	76	102 <sup>a</sup>
		100	250	3	6	10	14	22	29	38 <sup>a</sup>
		250	900	2	3	5	6	10	13	19 <sup>a</sup>
		900	3 500	1	2	3	5	6	10	13 <sup>a</sup>
3,2	6,5	100	900	2	3	6	9	14	19	25 <sup>a</sup>
		900	3 500	1	2	3	5	6	10	13 <sup>a</sup>
6,5	203		250	6	14	25	39	57	76	102 <sup>a</sup>
		250	450	2	3	6	10	15	20	25 <sup>a</sup>
		450	3 500	1	2	3	5	8	11	14 <sup>a</sup>

<sup>a</sup> For the product over 6 000 mm and up to and including 10 000 mm in length, the maximum value in this table shall be applied for any 6 000 mm length.

### 4.2 Flatness tolerances

Flatness tolerances for strip are not specified.

Flatness tolerances for sheet and plate are specified in [Table 10](#) and are expressed as a percentage of the length, *L*, and/or the width, *W*, and/or the measured chord length, *l*.

Deviation from flatness,  $d$ , resulting from arching, buckling, or edge waves is measured as shown in Figure 2 to Figure 5, using a lightweight straight edge and a feeler gauge, dial gauge, or scale, while the sheet or plate is resting on a horizontal base plate with the concave side upwards.


These tolerances do not apply to sheet and plate supplied in the O (annealed) or HX8 (hard temper) and over tempers.

These tolerances do not include end or corner turnup.

The maximum values for products exceeding the range of specified thickness and width shall be agreed upon between the purchaser and the supplier.

Table 10 — Flatness tolerances


Specified thickness mm		Total deviation %		Partial deviation (for a chord of at least 300 mm) $d_{max}/l$ %
Over	Up to and including	On length $d_{max}/L$	On width $d_{max}/W$	
0,20	0,50	by agreement	by agreement	by agreement
0,50	3,0	0,4	0,5	0,5
3,0	6,0	0,3	0,4	0,4
6,0	50	0,2	0,3	0,3
50	203	0,2	0,2	by agreement

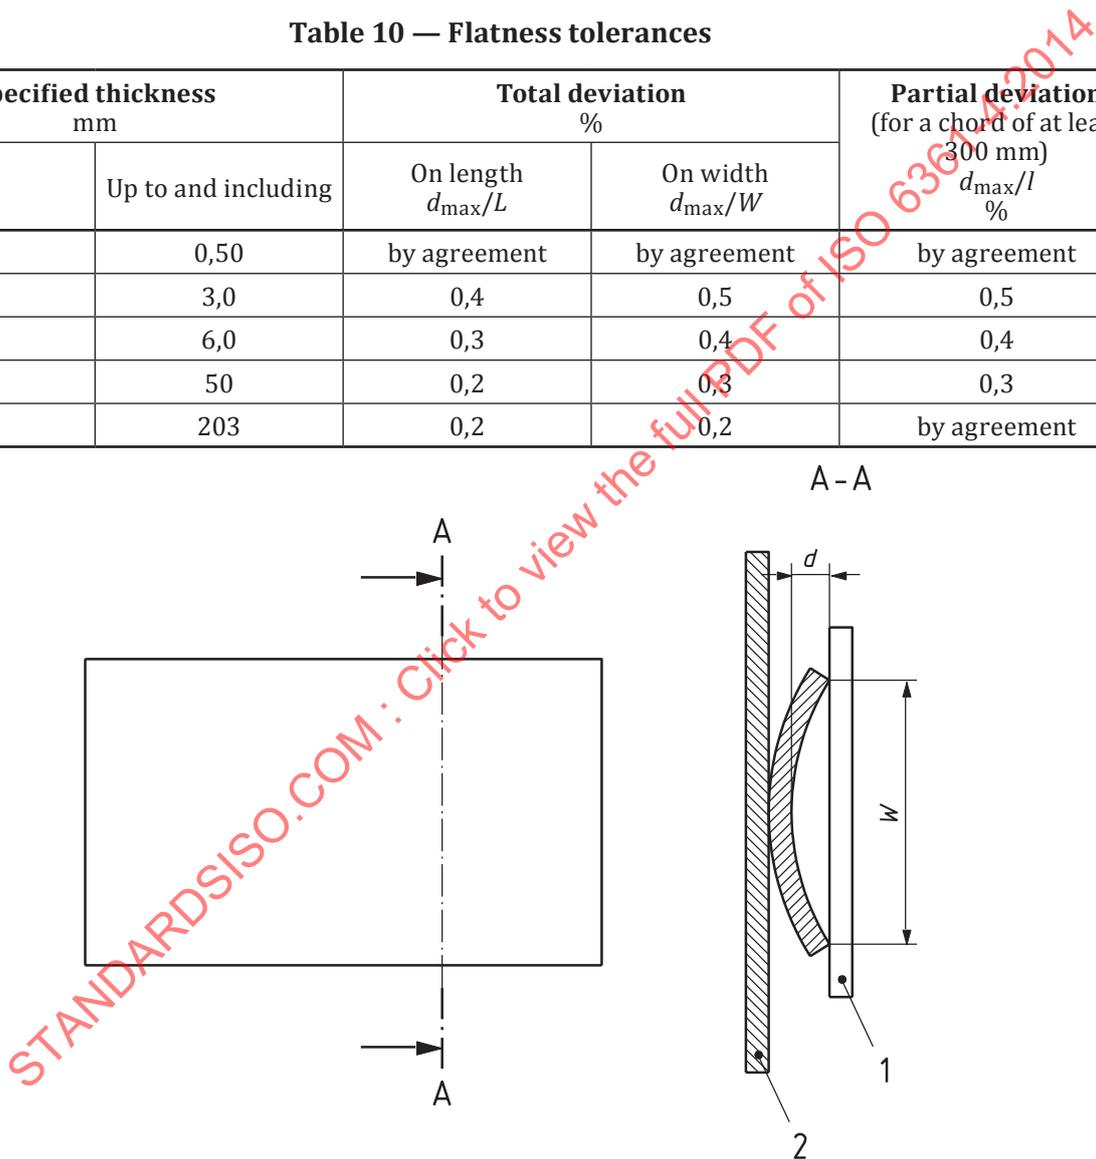

Key

- 1 straight edge
- 2 base plate
- $d$  deviation from flatness
- $W$  width of the sheet or plate


Figure 2 — Transverse arch

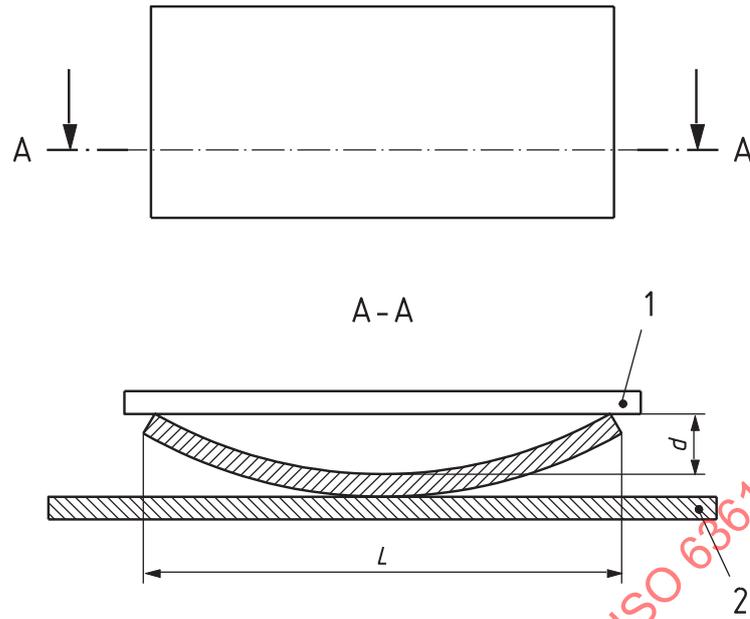

**Key**

- 1 straight edge
- 2 base plate
- $d$  deviation from flatness
- $L$  length of the sheet or plate


**Figure 3 — Longitudinal arch**

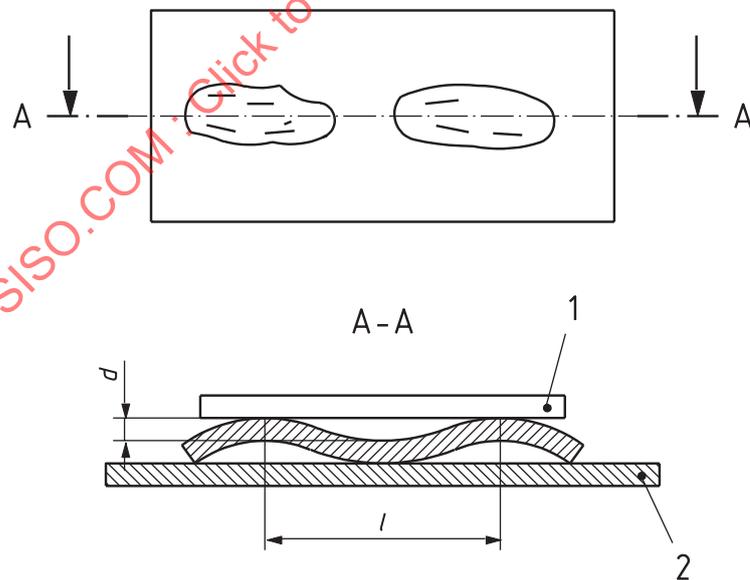

**Key**

- 1 straight edge
- 2 base plate
- $d$  deviation from flatness
- $l$  length of buckle (chord)

**Figure 4 — Buckles**

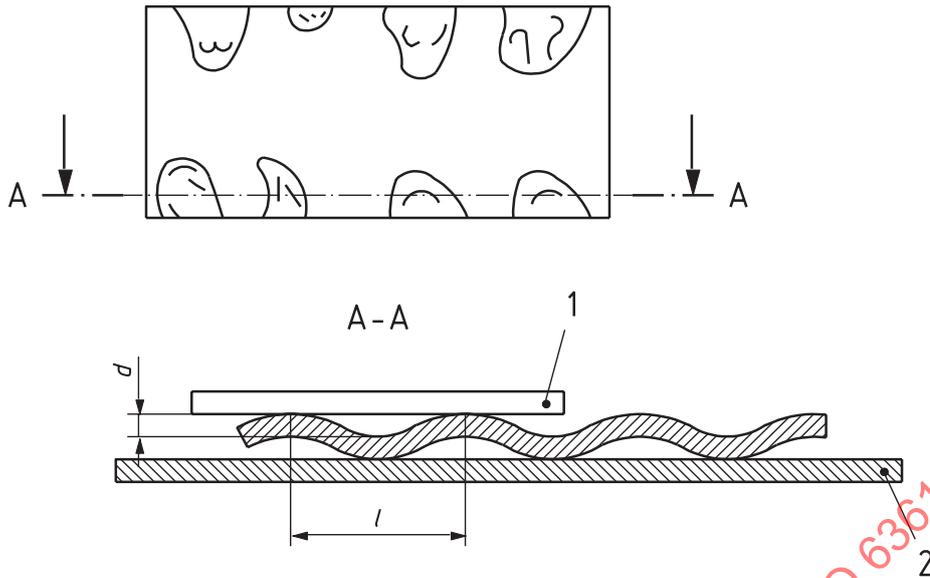

- Key**
- 1 straight edge
  - 2 base plate
  - d* deviation from flatness
  - l* length of edge wave (chord)

**Figure 5 — Edge waves**

**4.3 Squareness tolerances**

The diagonal distances between opposite corners of any sheet shall not differ by more than the values shown in [Table 11](#).

**Table 11 — Squareness tolerances**

Specified length mm	Specified width (mm) <i>W</i> <sup>a</sup>	
	Up to and including 900	Over 900
<b>Maximum value</b>		
Up to and including 3 700	$2,4 \times \frac{W}{300}$	$2,0 \times \frac{W}{300}$
Over 3 700	$3,6 \times \frac{W}{300}$	$2,8 \times \frac{W}{300}$

<sup>a</sup> See [Figure 6](#).

**NOTE** In the case where the specified width is not an exact multiple of 300 mm, the maximum value of squareness shall be determined by using the next larger exact multiple for the width. For example, when the specified width is 1 400 mm and the specified length 1 800 mm, the tolerance thereon shall be 2,0 mm × 5 (multiple) = 10 mm.