



AEROSPACE RECOMMENDED PRACTICE

ARP6225

Issued

2014-11

Aircraft Tire Inspection - In-Service Removal Criteria

RATIONALE

On the same aircraft it is possible to find tires from different manufacturers. Since each tire manufacturer may have different removal criteria for a specific condition, this ARP harmonizes this data and presents common criteria related to the tire size and type. This is a compilation of data extracted from tire manufacturers' Care and Service Manuals and also from in-service experience.

TABLE OF CONTENTS

1.	SCOPE	3
2.	REFERENCES	3
3.	BACKGROUND	3
4.	PROCEDURE	3
5.	TIRE REMOVAL CRITERIA	9
5.1	Tread Wear Criteria	10
5.1.1	Normal Wear	10
5.1.2	Uneven Wear (shoulder, center)	10
5.2	Tread Damage Criteria	13
5.2.1	Flat spots	13
5.2.2	Tread Rubber Reversion	13
5.2.3	Skid-Through Burst	14
5.2.4	Peeled Rib	15
5.2.5	Thrown Tread	15
5.2.6	Tread Cuts	16
5.2.7	Chevron Cutting	17
5.2.8	Groove Cracking	18
5.2.9	Rib Undercutting	19
5.2.10	Open Tread Splice	19
5.2.11	Rib Tearing	20
5.2.12	Tread Chipping and Chunking	20
5.3	Sidewall Damage Criteria	21
5.3.1	Cuts on the Sidewall	21
5.3.2	Circumferential Cracks	21
5.3.3	Weathering and Cracking	22
5.3.4	Bulge or Blister Criteria	22

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2014 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)

Tel: +1 724-776-4970 (outside USA)

Fax: 724-776-0790

Email: CustomerService@sae.org

SAE WEB ADDRESS:

<http://www.sae.org>

SAE values your input. To provide feedback
on this Technical Report, please visit
<http://www.sae.org/technical/standards/ARP6225>

5.4	Miscellaneous Criteria.....	23
5.4.1	Foreign Object Damage.....	23
5.4.2	Tire Contamination (Hydraulic Fluid, Fuel, Disinfectants, Runway and Airplane De-icers, Hydrocarbons, etc.).....	23
5.4.3	Tire Slippage on the Rim.....	24
6.	NOTES	24
FIGURE 1	RADIAL TIRE COMPONENTS NOMENCLATURE.....	4
FIGURE 2	BIAS TIRE COMPONENTS NOMENCLATURE	5
FIGURE 3	NORMAL WEAR	10
FIGURE 4	SHOULDER WEAR	11
FIGURE 5	CENTER WEAR.....	11
FIGURE 6	TYPICAL TIRE WEAR CHARACTERISTICS.....	12
FIGURE 7	FLAT SPOT.....	13
FIGURE 8	TREAD RUBBER REVERSION.....	14
FIGURE 9	SKID THROUGH.....	14
FIGURE 10	PEELED RIB	15
FIGURE 11	THROWN TREAD	16
FIGURE 12	TREAD CUT.....	17
FIGURE 13	CHEVRON CUTTING	18
FIGURE 14	GROOVE CRACKING	18
FIGURE 15	RIB UNDERCUTTING	19
FIGURE 16	OPEN TREAD SPLICE	19
FIGURE 17	RIB TEARING	20
FIGURE 18	TREAD CHIPPING AND CHUNKING.....	20
FIGURE 19	SIDEWALL CUT.....	21
FIGURE 20	CIRCUMFERENTIAL CRACK	21
FIGURE 21	SIDEWALL WEATHERING AND CRACKING.....	22
FIGURE 22	BULGES.....	22
FIGURE 23	FOREIGN OBJECT DAMAGE	23
FIGURE 24	CONTAMINATION	24
TABLE 1	SUMMARY OF REMOVAL CONDITIONS AND ACTIONS.....	6

SAENORM.COM. Click to view the full PDF of arp6225

1. SCOPE

This document is for establishing tire removal criteria of on-wing civil aircraft tires only. This document is primarily intended for use with commercial aircraft but may be used on other categories of civil aircraft as applicable. The criteria are harmonized with the Care and Service Manuals of the tire manufacturers for both radial and bias tires.

2. REFERENCES

- Bridgestone: Tire Specification & Maintenance Manual (June 2013)
- Goodyear: Tire Care and Maintenance Manual, January 2011 Version
- Michelin: Aircraft Tire Care & Service Manual, MAT-CSM-32-45-01 Rev D, January 2011
- Dunlop: Tyre Care Manual (DM1172), 25 January 2008 Version
- ARP5507, Aircraft Tire-to-Wheel Performance Characteristics
- AIR5541A, Recommended Actions When Disinfectants, De-icers, and Cleaners Come in Contact with Landing Gear Structure

3. BACKGROUND

Airframe Manufacturers often include on-aircraft criteria for tire inspection and removal in their Aircraft Maintenance Manuals (AMMs) that may not align with the various tire manufacturers Care and Service Manuals (CSMs). It is possible to find mixed configurations, i.e., tires of same size but from different manufacturers, on the same aircraft.

To better address airline requests, the Airframe Manufacturers have expressed an interest in having a common set of criteria harmonized across the tire manufacturers CSMs that could be incorporated into their AMMs as they relate to tire removal criteria. The tire industry agreed to issue a common document for on-aircraft Tire Removal Criteria.


4. PROCEDURE

A summary of the tire removal conditions and actions listed below is shown in Table 1 as a quick reference guide. The detailed descriptions for the on-wing tire removal categories listed below are given in the following sections.

- Tread Wear Criteria:
 - Normal Wear
 - Uneven Wear (shoulder, center)
- Tread Damage Criteria:
 - Flat Spots
 - Tread Rubber Reversion
 - Skid-Through Damage
 - Peeled Rib
 - Thrown Tread
 - Tread Cuts
 - Chevron Cutting
 - Groove Cracking
 - Rib Undercutting
 - Open Tread Splice
 - Rib Tearing
 - Tread Chipping and Chunking

- Sidewall Damage Criteria:
 - Cuts
 - Circumferential Cracks
 - Weathering and Cracking
- Blister and Bulge Criteria
- Miscellaneous Criteria:
 - Foreign Object Damage (FOD)
 - Tire Contamination
 - Tire Slippage on the Rim

The radial and bias tire components are shown in Figures 1 and 2. Due to design parameters, the actual tire may or may not contain all pictured components.

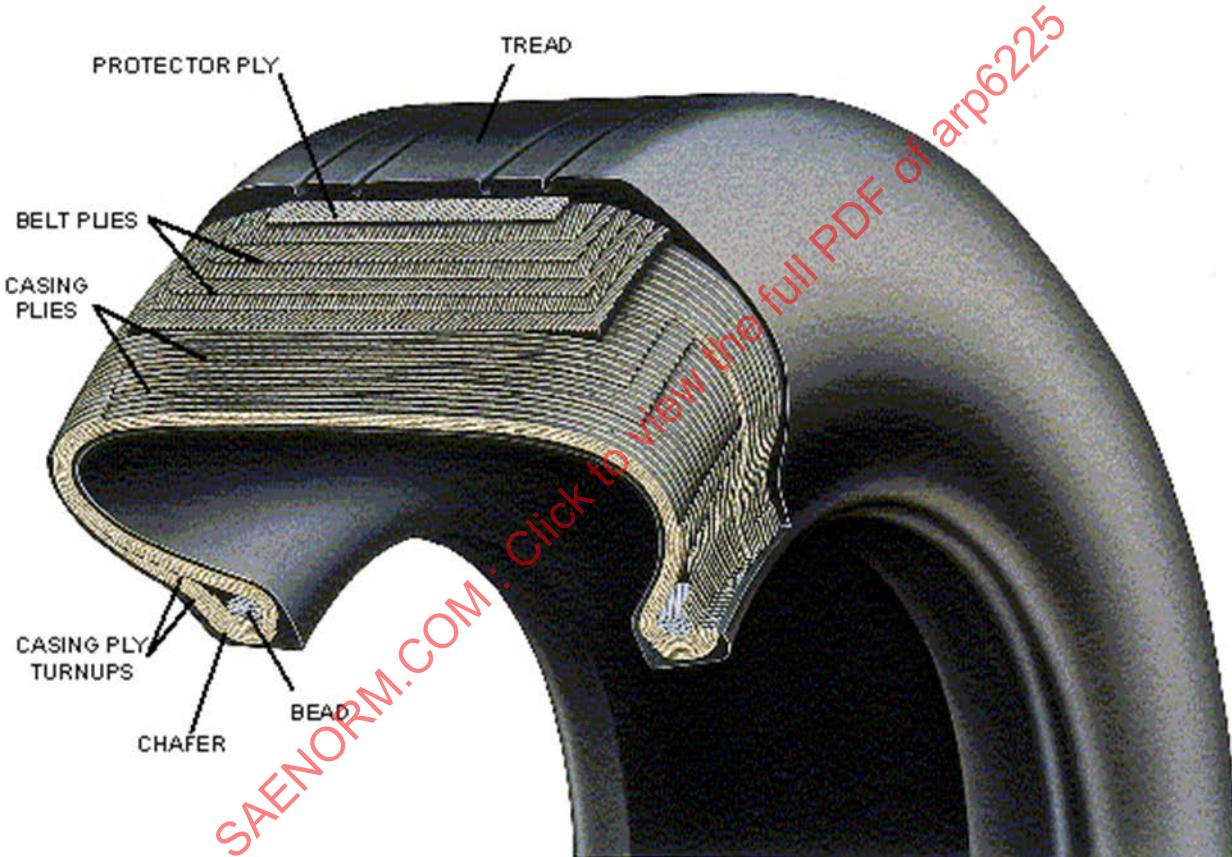

RADIAL AIRCRAFT TIRE CONSTRUCTION

FIGURE 1 - RADIAL TIRE COMPONENTS NOMENCLATURE

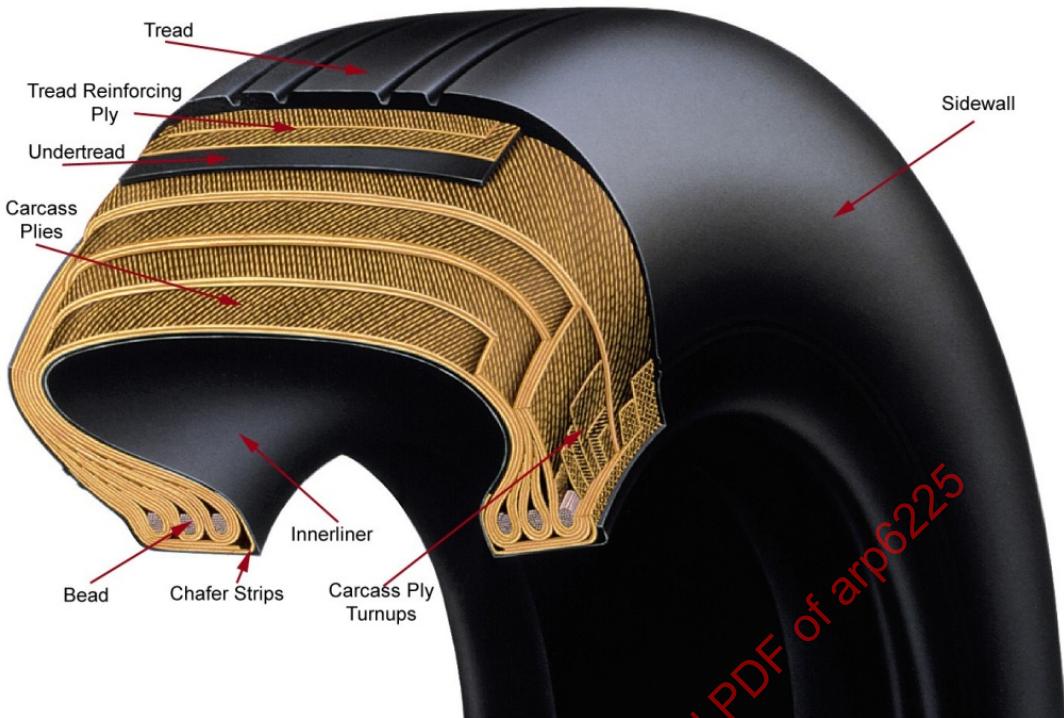


FIGURE 2 - BIAS TIRE COMPONENTS NOMENCLATURE

TABLE 1 - SUMMARY OF REMOVAL CONDITIONS AND ACTIONS

NOTE: This table is to be used as a QUICK REFERENCE for the removal conditions described in greater detail in the body of the document.

<u>TREAD WEAR CRITERIA</u>		
<u>CONDITION</u>	<u>OBSERVATION/DAMAGE</u>	<u>ACTION</u>
<u>Normal Wear</u>	An even tread wear indicates that the tire has been properly maintained during its service life.	<p>NORMAL REMOVAL WEAR LIMIT: When the wear level reaches the bottom of any groove at one point or up to 1/8 of the circumference (Figures 3 and 4).</p> <p>RETURN TO BASE WEAR LIMIT: If either the protector ply (radial) or the reinforcing ply (bias) is exposed at any location over the tread surface (Figure 5).</p>
<u>Uneven Wear (shoulder, center)</u>	<p>Under-inflation can lead to excessive tread shoulder wear. It will lead to high tire deflection and subsequent heat build-up which may result in severe tire damage. The cause for operating underinflated should be investigated by the operator and corrective actions taken.</p> <p>Over-inflation can accelerate the center tread wear, reduce tire traction, reduce the number of landings per tread and make the tire more susceptible to cutting and foreign object damage (FOD).</p>	Tires with uneven wear should be removed from the aircraft if the wear limits (defined under normal wear) are reached.
<u>TREAD DAMAGE CRITERIA</u>		
<u>CONDITION</u>	<u>OBSERVATION/DAMAGE</u>	<u>ACTION</u>
<u>Flat Spots</u>	Tread flat spot or severe tread rubber abrasion results from steering maneuvers prior to aircraft rolling, or the locking of the wheel during braking or touchdown. Flat spotting due to cold temperature or prolonged parking is not a condition for tire removal.	<p>The tire should be removed from the aircraft when:</p> <ol style="list-style-type: none"> 1) the flat spot damage exceeds the wear removal criteria of 5.1; or 2) the flat spot contributes to an unacceptable vibration condition (Figure 7).
<u>Tread Rubber Reversion</u>	Tread rubber reversion is generally caused by wheel locking on wet or ice covered runways. The affected area is similar in shape to a flat spot (oval), but the rubber appears to be melted (Figure 8).	<p>The tire should be removed from the aircraft when:</p> <ol style="list-style-type: none"> 1) the reversion flat spot damage exceeds the wear removal criteria of 5.1; or 2) an unacceptable vibration condition is experienced.
<u>Skid-Through Burst</u>	Skid-through burst results from the locking of the wheel. In this case, the tire experiences either a loss of inflation pressure or an explosive blowout. (Figure 9).	Both the failed tire and axle mate tire should be removed from the aircraft, the burst tire marked as "scrap" and the axle mate tire marked with the removal reason ("Mate to Flat"). The skid through tire can be scrapped locally but the mate to flat tire should be returned to the tire manufacturer or retreader.

<u>Peeled Rib</u>	A peeled rib usually starts with a cut or damage in the tread and results in a circumferential delamination of the tread rib away from the tire casing, typically with no loss of reinforcing plies (Figure 10) or tire pressure.	The tire should be removed immediately from service when the peeled section, regardless of length, is exposing fabric or has fully detached. Pieces from the tread should be requested from airport authorities and returned to the home base for potential analysis by the tire supplier.
<u>Thrown Tread</u>	A thrown tread on an inflated tire is a partial or complete loss of the tread down to the casing plies or tread reinforcing plies/protector ply (Figure 11).	The tire should be removed immediately from service. Pieces from the tread should be requested from airport authorities and returned to the home base for potential analysis by the tire supplier. If the damaged tire is not inflated due to a loss of inflation pressure, then the axle mate should be removed also. If the tire is still inflated after the aircraft is parked, record the tire pressure after it has cooled down (allow 3 hours).
<u>Tread Cuts</u>	Foreign objects that are present on runways, taxiways and parking areas can cause cuts to the tires (Figure 12).	Tire should be removed immediately from the aircraft if: <ul style="list-style-type: none"> the cut exposes or penetrates reinforcing ply (bias tire) or protector ply (radial tire), or the cut or damage severs or extends across a tread rib, or undercutting occurs at the base of any tread rib cut
<u>Chevron Cutting</u>	Chevron cutting is tread damage (small z-, s- or v-shaped tears) caused by touchdown, running and/or braking on cross-grooved runways (Figure 13). Chevron cutting is a condition of the tread rubber only.	Tire should be removed from aircraft if: <ul style="list-style-type: none"> The tread cut criteria are reached, or The tread reinforcing ply (bias tire) or protector ply (radial tire) is exposed for more than 1.0 square inch (6.45 cm^2), or The cutting involves the full width of any one of the tread ribs
<u>Groove Cracking</u>	Groove cracking may result from ozone attack of the rubber or excessive flexing of the groove bottoms as a result of insufficient inflation of the tire. These cracks occur along the bottom of tread grooves (Figure 14).	The tire should be removed immediately from the aircraft if: <ul style="list-style-type: none"> groove cracking exposes the reinforcing ply (bias tire) or the protector ply (radial tire) for more than 0.25 inch (6.35 mm) circumferentially in length. groove cracking has led to undercutting of the adjacent rib by more than 0.25 inch (6.35 mm).
<u>Rib Undercutting</u>	Rib undercutting can be an extension of groove cracking progressing under a tread rib or develop as a break in the groove wall extending under the rib. This can lead to tread chunking, peeled rib, or thrown tread (Figure 15).	The tire should be removed immediately from the aircraft if undercutting extends more than 0.25 inch (6.35 mm) under the tread rib.
<u>Open Tread Splice</u>	An open tread splice is a crack in the tread rubber where the manufacturing joint or splice separates in a radial direction across the tread ribs (Figure 16).	The tire having this defect should be removed immediately from the aircraft.
<u>Rib Tearing</u>	Rib tearing occurs when the tire is subjected to excessive side force during landing or taxiing (Figure 17).	The tire should be removed immediately from the aircraft if cords are exposed for more than 1.0 square inch (6.45 cm^2) or the damage extends the full width of the tread rib.

<u>Tread Chipping and Chunking</u>	This is a condition visible at the edge of the tread rib in which small amounts of rubber begin to separate from the tread surface. Tread chunking can be caused by rib undercutting, tight turning or a high lateral force applied to the tire tread (Figure 18). This can lead to rib undercutting under severe conditions.	The tire should be removed immediately from the aircraft if the reinforcing ply (bias) or protector ply (radial) is exposed.
---	---	--

SIDEWALL DAMAGE CRITERIA

<u>CONDITION</u>	<u>OBSERVATION/DAMAGE</u>	<u>ACTION</u>
<u>Cuts on the Sidewall</u>	Cuts on the sidewall are caused by damage from FOD (Figure 19).	The tire should be removed immediately from the aircraft if any sidewall cord is visible. Cuts in the rubber which do not reach the cord plies are not detrimental to tire performance but should be monitored at subsequent inspections. The tire can be left in service if the cuts do not reach the ply cords.
<u>Circumferential Cracks</u>	Circumferential cracks can be caused by a molding condition of the rubber or load shear and stress combined with low tire inflation pressure (Figure 20).	The tire should be removed immediately from the aircraft if sidewall cord is visible. If operating underinflated is suspected the operator should investigate and take corrective actions.
<u>Weathering and Cracking</u>	Weathering and cracking occur when tires are exposed to ozone or to direct sunlight for an extended period of time (Figure 21). An insufficient tire inflation pressure accelerates the phenomenon.	The tire should be removed immediately from the aircraft if the sidewall plies are visible. If operating underinflated is suspected the operator should investigate and take corrective actions.
<u>Blister or Bulge</u>	Operating conditions outside the tire specification can cause bulges or blisters on the tread or on the sidewalls (Figure 22). They normally indicate a separation of components. When present, these defects can be observed mainly in the shoulder area of the tire while it is still warm.	Any tire showing a bulge or blister should be removed immediately from the aircraft. Mark the affected area with a soft crayon before deflating the tire.

MISCELLANEOUS CRITERIA

<u>CONDITION</u>	<u>OBSERVATION/DAMAGE</u>	<u>ACTION</u>
<u>Foreign Object Damage (FOD)</u>	Foreign object damage (FOD) (Figure 23) occurs when material left on the runway, taxiway or ramp causes damage to tires, engines, or other aircraft structure. It is the most common cause for tires being removed before full wear out. Airport authorities should be notified when it can be confirmed that tire removals for FOD are prevalent.	Remove tires from the aircraft if: <ul style="list-style-type: none"> • Cuts, embedded objects or other injuries expose or penetrate the reinforcing plies (bias) or protector ply (radial). • Cuts, embedded objects or other injuries that do not expose or penetrate the reinforcing plies (bias) or protector ply (radial) and extends entirely across a tread rib (any depth).

<u>Tire Contamination (Hydraulic Fluid, Fuel, Disinfectants, Runway and Airplane De-icers, Hydrocarbons, etc.)</u>	<p>In case of contamination, check for rubber condition (Figure 24). The tire has to be cleaned quickly with commercially available denatured alcohol to remove the contaminant and then washed with a soap and water solution.</p>	<ul style="list-style-type: none"> • Ensure that the contaminated rubber surface is not swelled. An easy check is to push your finger nail into the contaminated surface, and in case of swelling, the nail will leave a permanent imprint. In this case the tire should be returned to the retreader for inspection / possible repair. • If the subject tire needs to be removed and sent to the retreader for inspection, clearly identify the tire by marking with white chalk "Contaminated Tire".
<u>Tire Slippage on the Rim</u>	<p>After installation of a new tire on the rim, some cycles on the aircraft may be necessary before the tire reaches its final position. During this period of time, a slippage of the tire on the rim may be observed (e.g., the red mark on the tire is no longer aligned with the inflation valve or the wheel heavy point if marked).</p>	<p>ARP5507 recommends a maximum slippage of 20 degrees following installation. ARP5507 further recommends that tires which move in excess of 20 degrees should be disassembled and evaluated for appropriate action.</p>

5. TIRE REMOVAL CRITERIA

WARNING: Aircraft tires should be mounted only with the proper equipment, instructions, and operator training. Serious injury may occur as a result of improper equipment or procedures.

WARNING: Always approach a tire/wheel assembly mounted on an aircraft from an oblique angle (direction of the tire's shoulder).

WARNING: Aircraft tire and wheel assemblies should be treated with the same care as any other high pressure vessel. Improper handling may lead to serious injury.

WARNING: Aircraft tires should always be inflated with a properly regulated dry nitrogen inflation source. Regulate the supply line to a pressure no greater than 1.5 times the operating inflation pressure. Inflating a tire without a pressure regulator presents a risk of personal injury and/or damage to equipment.

CAUTION: Be careful when handling, assembling and disassembling wheel components to avoid damage.

WARNING: Do not probe cuts or embedded objects while a tire is inflated. Such action could further damage a tire causing it to rupture resulting in personal injury or equipment damage.

WARNING: A tire/wheel assembly that has known damage should be allowed to cool to ambient temperature (a minimum of 3 hours) before the tire is deflated.

WARNING: Use care when removing the valve core from an inflated tire. Use of a valve core removal tool is recommended. The valve core of an inflated tire can be projected at a high speed and possibly cause injury.

NOTE: Tires removed for other than normal wear should be investigated for cause with corrective actions taken, if appropriate.

NOTE: The regular care and maintenance of aircraft tires while in service is essential to maximizing the number of duty cycles that can be achieved by each tire, and to minimizing the risk of aircraft damage from tire failures. It is important that tire condition and pressure are checked daily and underinflated tires should be addressed per the tire pressure maintenance schedule of ARP5265.

5.1 Tread Wear Criteria

5.1.1 Normal Wear

An even tread wear indicates that the tire has been properly maintained during its service life.

Removal Limit:

NORMAL REMOVAL WEAR LIMIT: When the wear level reaches the bottom of any groove at one point or up to 1/8 of the circumference (Figure 3):



FIGURE 3 - NORMAL WEAR

NOTE: When the NORMAL REMOVAL limit is reached, the tire should be replaced. If it is necessary to continue the tire in service beyond the normal wear limit, the tire should be removed either at the next maintenance base or upon reaching the RETURN TO BASE WEAR LIMIT, whichever occurs first. At the RETURN TO BASE LIMIT, the tire should be removed and replaced. In such a case however, the subject tire might not be suitable for retreading.

RETURN TO BASE WEAR LIMIT: If either the protector ply (radial) or the reinforcing ply (bias) is exposed at any location over the tread surface (Figure 4 or 5).

5.1.2 Uneven Wear (shoulder, center)

Under-inflation can lead to excessive tread shoulder wear. It will lead to high tire deflection and subsequent heat build-up which may result in severe tire damage. The cause for operating underinflated should be investigated by the operator and corrective actions taken.

Over-inflation can accelerate the center tread wear, reduce tire traction, reduce the number of landings per tread and make the tire more susceptible to cutting and foreign object damage (FOD).

REMOVAL LIMIT: Tires with uneven wear should be removed from the aircraft if the wear limits (defined under normal wear) are reached.



FIGURE 4 - SHOULDER WEAR



FIGURE 5 - CENTER WEAR

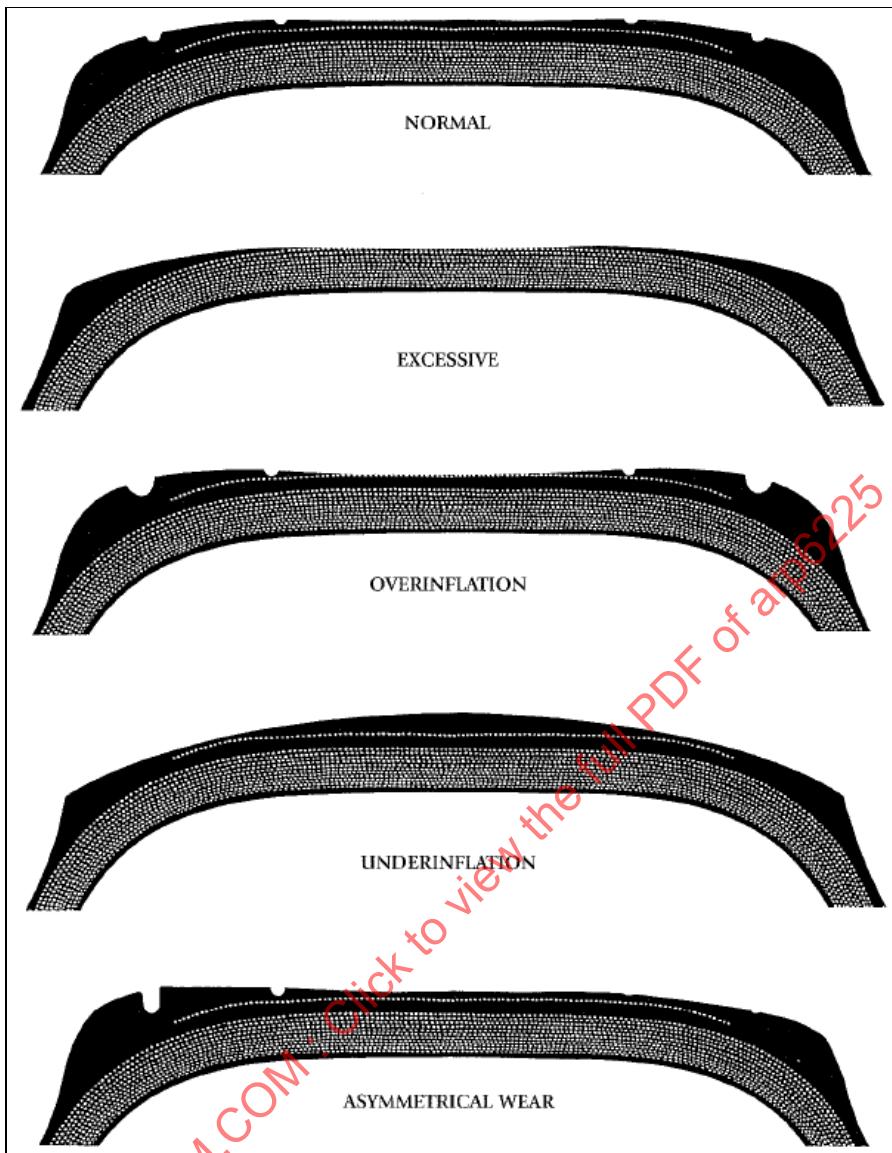


FIGURE 6 - TYPICAL TIRE WEAR CHARACTERISTICS

NOTE: When the NORMAL REMOVAL limit is reached, the tire should be replaced. If it is necessary to continue the tire in service beyond the normal wear limit, the tire should be removed either at the next maintenance base or upon reaching the RETURN TO BASE WEAR LIMIT, whichever occurs first. At the RETURN TO BASE LIMIT, the tire should be removed and replaced. In such a case however, the subject tire might not be suitable for retreading.

NOTE: Tires identified as operating underinflated for an unknown length of time with uneven wear may have some internal damage and could fail causing damage to the aircraft. Such tires should be removed at the first opportunity, but no later than when the above wear limits are reached. A visible bluing of the shoulder rubber may be one indication of the tire operated in an underinflated condition.

5.2 Tread Damage Criteria

5.2.1 Flat spots

Tread flat spot or severe tread rubber abrasion results from steering maneuvers prior to aircraft rolling, or the locking of the wheel during braking or touchdown. Flat spotting due to cold temperature or prolonged parking is not a condition for tire removal.

REMOVAL LIMIT: The tire should be removed from the aircraft when:

1. the flat spot damage exceeds the wear removal criteria of 5.1; or
2. the flat spot contributes to an unacceptable vibration condition (Figure 7).



Locked wheel tire flat spot



Typical tire flat spot

FIGURE 7 - FLAT SPOT

NOTE: The tire can remain in service if the flat spot does not reach the above-mentioned limit and if there is:

1. sufficient groove depth in the whole flat spot area;
2. no incipient (visible) separation; and
3. the vibration level is within an acceptable range during rolling.

5.2.2 Tread Rubber Reversion

Tread rubber reversion is generally caused by wheel locking on wet or ice covered runways. The affected area is similar in shape to a flat spot (oval), but the rubber appears to be melted (Figure 8).

REMOVAL LIMIT: The tire should be removed from the aircraft when:

1. the reversion flat spot damage exceeds the wear removal criteria of 5.1; or
2. an unacceptable vibration condition is experienced.



FIGURE 8 - TREAD RUBBER REVERSION

5.2.3 Skid-Through Burst

Skid-through burst results from the locking of the wheel. In this case, the tire experiences either a loss of inflation pressure or an explosive blowout (Figure 9).

REMOVAL LIMIT: Both the failed tire and axle mate tire should be removed from the aircraft, the burst tire marked as “scrap” and the axle mate tire marked with the removal reason (“Mate to Flat”). The skid through tire can be scrapped locally but the mate to flat tire should be returned to the tire manufacturer or retreader.



FIGURE 9 - SKID THROUGH

5.2.4 Peeled Rib

A peeled rib usually starts with a cut or damage in the tread and results in a circumferential delamination of the tread rib away from the tire casing, typically with no loss of reinforcing plies (Figure 10) or tire pressure.

REMOVAL LIMIT: The tire should be removed immediately from service when the peeled section, regardless of length, is exposing fabric or has fully detached. Pieces from the tread should be requested from airport authorities and returned to the home base for potential analysis by the tire supplier.



FIGURE 10 - PEELED RIB

5.2.5 Thrown Tread

A thrown tread on an inflated tire is a partial or complete loss of the tread down to the casing plies or tread reinforcing plies/protector ply (Figure 11).

NOTE: A thrown tread tire should not be reported as a burst tire unless the tire experienced a rapid pressure loss concurrent with the thrown tread.

NOTE: Inspection of the aircraft after a tire burst, thrown tread, or wheel failure should be completed prior to release of the aircraft.

REMOVAL LIMIT: The tire should be removed immediately from service. Pieces from the tread should be requested from airport authorities and returned to the home base for potential analysis by the tire supplier. If the damaged tire is not inflated due to a loss of inflation pressure, then the axle mate should be removed also.



FIGURE 11 - THROWN TREAD

If the tire is still inflated after the aircraft is parked, record the tire pressure after it has cooled down (allow 3 hours).

NOTE: Early signs of tread separation can manifest themselves in the form of tread bulges, local uneven wear (depression) or local tread/sidewall rubber split.

5.2.6 Tread Cuts

Foreign objects that are present on runways, taxiways and parking areas can cause cuts to the tires (Figure 12).

REMOVAL LIMIT: Tire should be removed immediately from the aircraft if:

- the cut exposes or penetrates reinforcing ply (bias tire) or protector ply (radial tire), or
- the cut or damage severs or extends across a tread rib, or
- undercutting occurs at the base of any tread rib cut

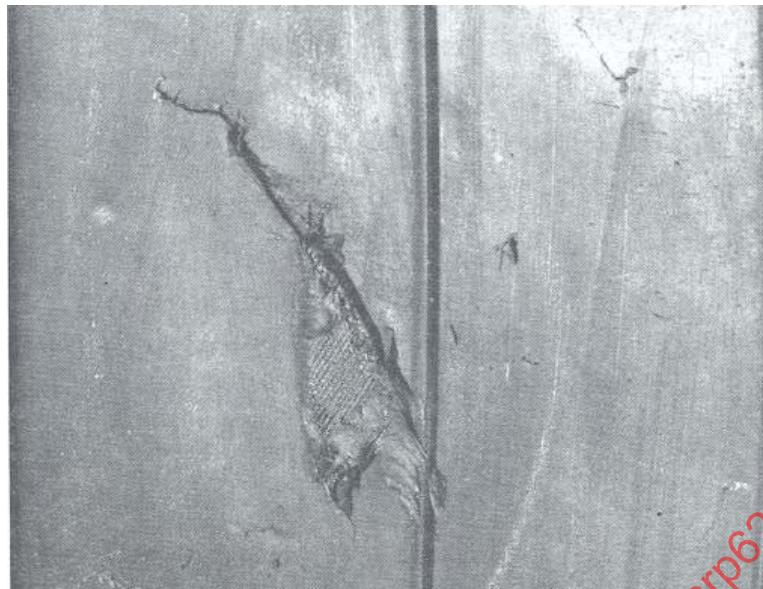


FIGURE 12 - TREAD CUT

NOTE: Mark all cuts, foreign object damage (FOD), or leak sites while the tire is still inflated. Damage can be difficult to locate when the tire is deflated.

5.2.7 Chevron Cutting

Chevron cutting is tread damage (small z-, s- or v-shaped tears) caused by touchdown, running and/or braking on cross-grooved runways (Figure 13). Chevron cutting is a condition of the tread rubber only.

REMOVAL LIMIT: Tire should be removed from aircraft if:

- The tread cut criteria are reached, or
- The tread reinforcing ply (bias tire) or protector ply (radial tire) is exposed for more than 1.0 square inch (6.45 cm^2), or
- The cutting involves the full width of any one of the tread ribs



FIGURE 13 - CHEVRON CUTTING

5.2.8 Groove Cracking

Groove cracking may result from ozone attack of the rubber or excessive flexing of the groove bottoms as a result of insufficient inflation of the tire. These cracks occur along the bottom of tread grooves (Figure 14).

REMOVAL LIMIT: The tire should be removed immediately from the aircraft if:

- groove cracking exposes the reinforcing ply (bias tire) or the protector ply (radial tire) for more than 0.25 inch (6.35 mm) circumferentially in length.
- groove cracking has led to undercutting of the adjacent rib by more than 0.25 inch (6.35 mm).



FIGURE 14 - GROOVE CRACKING

5.2.9 Rib Undercutting

Rib undercutting can be an extension of groove cracking progressing under a tread rib or develop as a break in the groove wall extending under the rib. This can lead to tread chunking, peeled rib, or thrown tread (Figure 15).

REMOVAL LIMIT: The tire should be removed immediately from the aircraft if undercutting extends more than 0.25 inch (6.35 mm) under the tread rib.



FIGURE 15 - RIB UNDERCUTTING

5.2.10 Open Tread Splice

An open tread splice is a crack in the tread rubber where the manufacturing joint or splice separates in a radial direction across the tread ribs (Figure 16).

REMOVAL LIMIT: The tire having this defect should be removed immediately from the aircraft.



FIGURE 16 - OPEN TREAD SPLICE